

AEC RESEARCH AND DEVELOPMENT REPORT

ORNL-2150
C-84 - Reactors-Special
Features of Aircraft Reactors


ORNL MASTER COPY

A PHYSICAL PROPERTY SUMMARY FOR ANP FLUORIDE MIXTURES

S. I. Cohen
W. D. Powers
N. D. Greene

Evelyn Martin AEC 11-24-59 declass

1212315

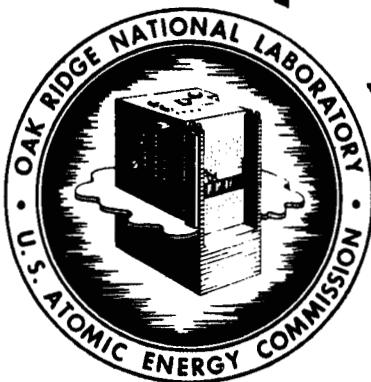

OAK RIDGE NATIONAL LABORATORY
OPERATED BY

UNION CARBIDE NUCLEAR COMPANY

A Division of Union Carbide and Carbon Corporation

UCN

POST OFFICE BOX P • OAK RIDGE, TENNESSEE

LEGAL NOTICE

This report was prepared as an account of Government sponsored work. Neither the United States, nor the Commission, nor any person acting on behalf of the Commission:

- A. Makes any warranty or representation, express or implied, with respect to the accuracy, completeness, or usefulness of the information contained in this report, or that the use of any information, apparatus, method, or process disclosed in this report may not infringe privately owned rights; or
- B. Assumes any liabilities with respect to the use of, or for damages resulting from the use of any information, apparatus, method, or process disclosed in this report.

As used in the above, "person acting on behalf of the Commission" includes any employee or contractor of the Commission to the extent that such employee or contractor prepares, handles or distributes, or provides access to, any information pursuant to his employment or contract with the Commission.

ORNL-2150

C-84 Aircraft Reactors

This document consists of 120
pages. Copy 90 of 326 copies.
Series A.

Contract No. W-7405, eng 26

Reactor Experimental Engineering Division

A PHYSICAL PROPERTY SUMMARY FOR ANP FLUORIDE MIXTURES

by

S. I. Cohen
W. D. Powers
N. D. Greene

DATE ISSUED AUG 23 1956

OAK RIDGE NATIONAL LABORATORY
Operated by
UNION CARBIDE NUCLEAR COMPANY
A Division of Union Carbide and Carbon Corporation
Post Office Box Y
Oak Ridge, Tennessee

INTERNAL DISTRIBUTION

1. A. A. Abbatiello
2. R. G. Affel
3. P. A. Agron
4. L. G. Alexander
5. G. M. Adamson
6. J. C. Amos
7. M. A. Bredig
8. G. E. Boyd
9. R. B. Briggs
10. E. G. Bohlmann
11. M. Bender
12. W. F. Boudreau
13. W. E. Browning
14. E. S. Bettis
15. C. M. Blood
16. H. J. Buttram
17. J. P. Blakely
18. F. F. Blankenship
19. M. Blander
20. E. P. Blizzard
21. F. R. Bruce
22. D. S. Billington
23. C. D. Baumann
24. C. R. Baldock
25. C. J. Barton
26. F. L. Culler
27. C. R. Croft
28. S. Cantor
29. C. E. Center (K-25)
30. B. H. Clampitt
31. D. R. Cuneo
32. S. I. Cohen
33. C. M. Copenhaver
34. D. D. Cowen
35. R. S. Carlsmith
36. W. R. Chambers
37. W. G. Cobb
38. W. B. Cottrell
39. S. J. Cromer
40. G. A. Christy
41. A. D. Callihan
42. C. E. Clifford
43. M. M. Cooper
44. D. Garrison
45. W. H. Cook
46. F. A. Doss
47. J. H. Devan
48. L. M. Doney
49. E. R. Dytko
50. W. K. Eister
51. L. B. Emlet (K-25)
52. J. E. Eorgan
53. E. P. Epler
54. W. K. Ergen
55. A. P. Fraas
56. W. T. Furgerson
57. H. A. Friedman
58. D. E. Ferguson
59. M. J. Feldman
60. R. A. Gilbert
61. J. B. Gregg
62. H. E. Goeller
63. R. J. Gray
64. W. R. Gambill
65. N. D. Greene
66. D. P. Gregory
67. H. C. Gray
68. R. I. Gray
69. W. R. Grimes
70. H. W. Hoffman
71. E. E. Hoffman
72. D. C. Hamilton
73. W. H. Jordan
74. G. W. Keilholtz
75. J. J. Keyes
76. E. E. Ketchen
77. F. Kertesz
78. F. A. Knox
79. M. T. Kelley
80. F. L. Keller
81. B. Kinyon
82. P. R. Kasten
83. R. B. Korsmeyer
84. A. S. Kitzes
85. R. B. Lindauer
86. R. N. Lyon
87. J. A. Lane
88. C. G. Lawson
89. S. Langer
90. F. E. Lynch

- | | |
|--------------------------|---|
| 91. M. E. Lackey | 128. B. J. Sturm |
| 92. G. L. Muller | 129. G. F. Schenck |
| 93. R. E. MacPherson | 130. M. J. Skinner |
| 94. W. D. Manly | 131. B. E. Thomas |
| 95. L. A. Mann | 132. N. V. Smith |
| 96. E. R. Mann | 133. O. Sisman |
| 97. C. Mantell | 134. G. P. Smith |
| 98. W. B. McDonald | 135. C. D. Susano |
| 99. F. R. McQuilkin | 136. R. J. Sheil |
| 100. R. V. Meghrebian | 137. A. W. Savolainen |
| 101. R. P. Milford | 138. H. W. Savage |
| 102. R. E. Moore | 139. R. D. Schultheiss |
| 103. R. E. Meadows | 140. W. L. Scott |
| 104. H. P. Metcalf | 141. S. C. Shuford |
| 105. A. J. Miller | 142. L. E. Topol |
| 106. A. S. Meyer, Jr. | 143. D. G. Thomas |
| 107. J. R. McNally, Jr. | 144. J. Truitt |
| 108. F. C. Maienschein | 145. D. B. Trauger |
| 109. H. G. MacPherson | 146. W. F. Vaughan |
| 110. J. P. Murray (Y-12) | 147. E. R. Van Artsdal |
| 111. G. J. Nessle | 148. G. D. White |
| 112. R. F. Newton | 149. G. M. Watson |
| 113. R. H. Nimmo | 150. W. T. Ward |
| 114. L. G. Overholser | 151. J. C. Wilson |
| 115. R. W. Peelle | 152. J. C. White |
| 116. M. B. Panish | 153. J. L. Wantland |
| 117. L. D. Palmer | 154. C. S. Walker |
| 118. H. F. Poppendiek | 155. A. M. Weinberg |
| 119. W. D. Powers | 156. G. D. Whitman |
| 120. A. M. Perry | 157. C. E. Winters |
| 121. M. W. Rosenthal | 158. M. M. Yarosh |
| 122. REED Library | 159. J. Zasler |
| 123. J. D. Redman | 160. D. Zucker |
| 124. M. T. Robinson | 161-162. Central Research Library |
| 125. J. A. Swartout | 163-164. ORNL - Y-12 Technical Library,
Document Reference Section |
| 126. I. Spiewak | 165-200. Laboratory Records Department |
| 127. B. A. Soderberg | 201. Laboratory Records, ORNL R.C. |

EXTERNAL DISTRIBUTION

- | |
|--|
| 202. AF Plant Representative, Burbank |
| 203. AF Plant Representative, Baltimore |
| 204. AF Plant Representative, Marietta |
| 205-207. AF Plant Representative, Santa Monica |
| 208-209. AF Plant Representative, Seattle |
| 210. AF Plant Representative, Wood-Ridge |
| 211. Air Materiel Area |
| 212. Air Research and Development Command (RDGN) |
| 213. Air Technical Intelligence Center |
| 214. Bureau of Aeronautics, General Representative |

- 215. Allison Division
- 216-218. ANP Project Office, Fort Worth
- 219. Albuquerque Operations Office
- 220. Argonne National Laboratory
- 221. Armed Forces Special Weapons Project, Sandia
- 222. Armed Forces Special Weapons Project, Washington
- 223. Assistant Secretary of the Air Force, R&D
- 224-230. Atomic Energy Commission, Washington (1 copy to R. H. Graham)
- 231-232. Battelle Memorial Institute (1 copy to E. M. Simons)
- 233-234. Bettis Plant (WAPD)
- 235. Bureau of Aeronautics
- 236. Bureau of Aeronautics (Code 24)
- 237. Chicago Operations Office
- 238. Chief of Naval Research
- 239. Chicago Patent Group
- 240. Convair-General Dynamics Corporation
- 241. Engineer Research and Development Laboratories
- 242-245. General Electric Company (ANPD)
- 246. Hartford Area Office
- 247. Headquarters Air Force Special Weapons Center
- 248. Idaho Operations Office
- 249-250. Knolls Atomic Power Laboratory (1 copy to W. J. Robb, Jr.)
- 251. Lockland Area Office
- 252. Los Alamos Scientific Laboratory
- 253. National Advisory Committee for Aeronautics, Cleveland
- 254. National Advisory Committee for Aeronautics, Washington
- 255. Naval Air Development and Material Center
- 256-258. Naval Research Laboratory (1 copy ea. to C. T. Ewing and R. R. Miller)
- 259. New York Operations Office
- 260. North American Aviation, Inc. (Aerophysics Division)
- 261. Nuclear Development Corporation of America
- 262. Office of the Chief of Naval Operations (OP-361)
- 263. Patent Branch, Washington
- 264-275. Pratt & Whitney Aircraft Division (Fox Project) (1 copy ea. to C. C. Bigelow, A. I. Chalfant, M. S. Freed, W. S. Farmer, M. Hoenig, S. M. Kepelner, and R. I. Strough and Fox Project Library)
- 276. R. G. Rowe, P.O. Box 481, Van Nuys, California
- 277. San Francisco Operations Office
- 278. Sandia Corporation
- 279. School of Aviation Medicine
- 280. Sylvania Electric Products, Inc.
- 281. USAF Project Rand
- 282. University of California Radiation Laboratory, Livermore
- 283-300. Wright Air Development Center (WCOSI-3)
- 301-325. Technical Information Service Extension, Oak Ridge
- 326. Division of Research and Development, AEC, ORO

FOREWORD

For the past five years the Heat Transfer and Physical Properties Section of ORNL has investigated some of the physical properties of fluoride mixtures of specific interest to the ANP Project. Particular attention has been given to the "thermal properties", namely, the density, heat capacity, viscosity, and thermal conductivity, because of the important role that they play in the heat and momentum transfer processes in ANP reactors. A limited study of the electrical conductivity and surface tension of molten fluorides was also conducted.

During the first few years of this research task, a large part of the group effort was directed toward the investigation and evaluation of techniques and devices by which these properties could be measured accurately in the temperature range of about 1000°F to 1800°F. The necessity of operating equipment at such high temperature levels as well as in controlled inert atmospheres often made it impossible to use prosaic property equipment. Consequently many new devices had to be developed.

The earlier summaries of the physical properties measurements for fluorides were presented in the form of ORNL memoranda; some of these data were designated as "preliminary" because measuring techniques were still in the process of being refined and because the chemical purities of fluoride samples were at times inadequate. The experimental data summarized in this report in most cases were obtained by two independent measurement techniques; also, it is believed that most of the samples used were relatively pure. Although much progress has been made in the art and science of making these difficult measurements, further refinements should be and are being made, particularly in the case of thermal conductivity measurements for liquids.

General interpretations and correlations of these physical property data in terms of the known theoretical and semi-theoretical relations have been and are being made for the fluoride measurements. Such studies have already been reported in some of the topical reports on individual properties (see for example, ORNL 1702 and 1956). Additional topical reports on thermal properties are in the process of preparation.

In general, the molten fluorides are good heat transfer media because their thermal conductivities, thermal capacities per unit volume, and densities are high and their viscosities and vapour pressures are reasonable; the following tabulation gives the approximate ranges over which each of the thermal properties varies:

thermal conductivity: 0.5 to 2.6 Btu/hr-ft²-(°F/ft)

thermal capacity per unit volume: 0.7 to 1.3 cal/cm³-°C

density: 2 to 4.5 gm/cc

viscosity: 2 to 12 centipoise

These thermal properties influence the heat and momentum transfer in reactor cores and heat exchangers in more or less complicated ways depending upon the system geometry and the fluid flow regime. Hence, it is not possible to rate a heat transfer fluid on the basis of its properties alone. However, detailed studies of the effectiveness of molten fluorides as reactor coolants and fuels (for a range of system geometries and flow conditions) have been conducted and presented in the ANP literature (see for example references 48 and 49).

Within the last year or two, several external organizations have initiated thermal property research on fluoride mixtures. The National Bureau of Standards and the Naval Research Laboratory have made heat capacity measurements and the

Mound Laboratory has made density and viscosity determinations. The Battelle Memorial Institute and the Mound Laboratory have started thermal conductivity research on these liquids.

The Heat Transfer and Physical Properties Section wishes to acknowledge the cooperation received from two of the Laboratory's Divisions. The former Materials Chemistry Division prepared the many samples which were needed in the study; valuable information on melting temperatures, vapor pressures, and phase diagrams of molten fluoride mixtures were also supplied. The Metallurgy Division performed complicated welding tasks in connection with some of the physical property devices.

H. F. Poppendiek
H. F. Poppendiek

TABLE OF CONTENTS

	Page
FOREWORD	v
SUMMARY-----	1
INTRODUCTION-----	2
A. DENSITY-----	2
B. HEAT CAPACITY-----	3
C. THERMAL CONDUCTIVITY-----	4
D. VISCOSITY-----	5
E. ELECTRICAL CONDUCTIVITY-----	6
F. SURFACE TENSION-----	6
G. TABLE I: ACCURACY SUMMARY-----	7
H. TABLE II: TABULATION OF MIXTURES ACCORDING TO CHEMICAL SYSTEM	8
TABULATED FLUORIDE PROPERTY DATA-----	9
VISCOSITY WORKSHEET-----	109
CONCLUDING REMARKS-----	110
REFERENCES-----	111

SUMMARY

This report presents a summary of certain physical properties that have been determined experimentally on the fluoride mixtures that have been formulated within the ANP program at ORNL (Refs. 1, 2). These properties include the density, enthalpy, heat capacity, heat of fusion, thermal conductivity, viscosity, Prandtl number, electrical conductivity and surface tension. In addition to the experimental data, values have been predicted for the heat capacity and density of the other mixtures from the correlations of these properties. Estimates of the viscosity have also been made for a number of the mixtures on which no experimental data were available.

INTRODUCTION

This report presents a compilation of certain physical properties that have been determined experimentally or predicted from correlations of experimental data for mixtures of fluorides that have been formulated within the ANP program (Ref. 1, 2). Each individual page of the tabulation is devoted to a summary of all of the known properties for a mixture together with the composition in mole and weight percent, the average molecular weight, and the liquidus temperature.

This introductory section will present brief discussions of each of the properties, providing short descriptions of the experimental systems used and statements regarding the accuracy of the data. Also included in this section is a tabulation of the mixture numbers arranged according to chemical system.

A. Density.

Density measurements have been made on sixteen molten fluoride mixtures. In addition, about nine mixtures containing BeF_2 have been studied at Mound Laboratory¹. Measurements were made by the buoyancy principle using a plummet suspended in the molten salt from an analytical balance. An error analysis indicated that the values reported are within $\pm 5\%$ of the true values. The results are reported in gms/cc as a function of $^{\circ}\text{C}$ and in lbs/ ft^3 as a function of $^{\circ}\text{F}$.

¹A large number of fluoride mixtures other than those reported here have been studied at Mound Laboratory. However, the contents of this report will be limited to mixtures which have been assigned composition numbers within the ANP project at this laboratory.

Work at Mound is being carried out by B. C. Blanke, aided at present by E. N. Bousquet and E. L. Murphy and in the past by L. V. Jones, K. W. Foster and R. E. Vallee. The density (and viscosity) program there at present involves a thorough investigation of systems containing the alkali fluorides with BeF_2 and UF_4 .

Predicted values are given for all the mixtures for which densities have not been experimentally studied. The values given for non-BeF₂ mixtures are based on an empirical correlation using the experimental data available (Ref. 16). The densities of mixtures containing BeF₂ have been predicted from a similarly developed but slightly different correlation using the experimental data taken on BeF₂-bearing mixtures at Mound Laboratory. These relationships correlate the experimental values to within $\pm 5\%$ and it is felt that the predicted values are of comparable accuracy.

Solid densities at room temperature have been measured for fifteen mixtures. The measurements were made by the buoyancy principle; samples of salt were weighed in air and then in toluene. An error analysis indicated errors of no more than $\pm 5\%$. Solid densities were calculated for the remainder of the mixtures by a simple formula involving the method of mixtures (Ref. 16). These calculated values agreed within $\pm 10\%$ with the experimental values available in most cases; however, a larger deviation was observed in one case which may be attributed to structural complexities.

Values of the volumetric coefficient of liquid expansion, β_L , were calculated from the experimental or predicted density data using the equation:

$$\beta_L = - \frac{1}{\rho} \left(\frac{d\rho}{dT} \right)_P$$

where $\left(\frac{d\rho}{dT} \right)_P$ is the slope of the density-temperature function. Values have been calculated at 700°C except when specified otherwise.

B. Heat Capacity.

The enthalpies, heats of fusion and heat capacities of twenty-one salt mixtures have been determined experimentally by dropping samples at various temperatures into

calorimeters and then measuring the amount of heat liberated. The heat capacity is the slope of the enthalpy-temperature relation thus obtained. Two types of calorimeters have been used. One was an ice calorimeter in which the heat given up by the sample melted ice in an ice-water mixture. The amount of ice melted was proportional to the amount of heat transferred and was determined by the volume change in the ice-water mixture. The other calorimeter was a copper block device. The amount of heat liberated by the sample was measured by the temperature rise of a large mass of copper. From the experimental values obtained for the particular fluorides studied, correlations have been found which enable one to predict the heat capacities of other mixtures (Ref. 4). Hence, estimates have been made of the heat capacities of all the mixtures not studied experimentally. The accuracies of the heat capacities determined experimentally are believed to be within $\pm 10\%$ of the true values; the predicted values are believed to be in error by no more than $\pm 20\%$.

The heats of fusion for the fluoride mixtures were obtained directly from the enthalpy-temperature relations.

C. Thermal Conductivity.

Thermal conductivities of seven mixtures in the liquid state have been measured by variable gap devices (Ref. 11). The conductivity is determined by measuring the temperature gradient across a liquid layer as well as the heat flow through it. The layer thickness is varied so that it is possible to eliminate the effect of interface resistances that may exist in the cell. The thermal conductivities of several liquids were determined in a constant gap device. Great difficulty was encountered when using this device because it was difficult to fill the cell completely with the sample liquid. Two methods have been used to measure solid

thermal conductivities; one is a steady state technique in which heat is passed through a slab of the solid salt, and the other is a transient method in which the time-temperature behavior of a solid sphere of the salt is studied.

Error analyses of liquid thermal conductivity measurements indicated that the errors were less than $\pm 25\%$. It is believed that the solid thermal conductivities are known more accurately than the liquid values. Consequently, liquid conductivities in particular are considered to be of a preliminary nature at this time. Improved conductivity devices are being designed to increase the accuracy. The temperature dependence of the conductivities of fluoride mixtures is currently being studied; the results indicate that the variation is not a large one. Thus, only mean conductivities are reported here.

D. Viscosity.

Viscosity measurements have been made on thirty-eight molten fluoride mixtures. Thirty-two of these were studied at ORNL and nine at Mound Laboratory², three being investigated at both laboratories.³ Measurements at ORNL were made with two devices; one of these is a capillary efflux viscometer and the other is a modified Brookfield rotational device. Measurements were made at Mound with a rotational viscometer developed there.

The values are presented in c.g.s. units and in engineering units. Kinematic viscosities are given as well as absolute viscosities. In addition, the viscosity of each salt is presented in terms of the usual exponential formula for viscosity:

$$\mu = A e^{B/T^0 K}$$

²A number of measurements have been made at Mound which are not reported here (see footnote 1, page 4).

³The results obtained independently at the two laboratories were in satisfactory agreement; the average values are reported here.

Agreement between the values determined by the two different instruments indicated that the results reported are within $\pm 10\%$ of the true values.

Predicted viscosities are given for a number of salts on which no measurements were made. These estimates were based on measurements on fluorides of similar compositions. These predicted values are probably within $\pm 20\%$ of the actual values.

A blank sheet of graph paper specially prepared for plotting viscosity data is furnished at the end of this report to facilitate interpolation and extrapolation of the values reported.

E. Electrical Conductivity.

The data on electrical conductivity included in this report were primarily obtained by means of a current-potential type cell (Ref. 13). This device measured directly the amount of current flow for a given voltage drop across a molten salt sample. Measurements were made on five molten fluoride mixtures. Since redeterminations of the conductivities of molten LiNO_3 , KNO_3 , and NaOH were made within $\pm 10\%$ of the values reported in the literature, it was felt that the fluoride measurements were in error by no more than this amount.

F. Surface Tension.

Surface tension measurements were made on one fluoride mixture, Composition 30, using a system consisting of a platinum ring supported from a calibrated wire spring which could be raised and lowered with a vernier (Ref. 21). A thermocouple probe was used to measure the surface temperature of the molten fluoride as accurately as possible.

G. Accuracy Summary.

The following is a summary of the accuracy limits for the properties presented in this report:

TABLE 1

	Error Limits for Experimental Measurements	Error Limits for Predicted or Estimated Values
Density (Solid)	$\pm 5\%$	----
Density (Liquid)	$\pm 5\%$	$\pm 5\%$
Heat Capacity	$\pm 10\%$	$\pm 20\%$
Thermal Conductivity	$\pm 25\%$	----
Viscosity	$\pm 10\%$	$\pm 20\%$
Electrical Conductivity	$\pm 10\%$	----
Surface Tension	----	----

H. Tabulation of Mixtures According to Chemical System.

The following table lists the mixture numbers arranged according to chemical system.

TABLE II

Binary Coolants		Corresponding Ternary Fuels	
System	Mixtures	System	Mixtures
NaF-ZrF ₄	28, 29, 31, 32, 34, 45, C test, 71, 83	NaF-ZrF ₄ -UF ₄	27, 30, 33, 38, 39, 40, 41, 42, 44, 46, 70, 99, 108
		NaF-ZrF ₄ -UF ₃	49
NaF-BeF ₂	35, 77, 113	NaF-BeF ₂ -UF ₄	1, 3, 16, 17, 36, 76, 92
LiF-BeF ₂	74, 112	LiF-BeF ₂ -UF ₄	75
LiF-NaF	100	LiF-NaF-UF ₄	18, 101
LiF-KF	102	LiF-KF-UF ₄	103
LiF-RbF	104	LiF-RbF-UF ₄	105
KF-BeF ₂	114, 116		
RbF-BeF ₂	115	NaF-KF-UF ₄	2, 2a, 4, 7
		NaF-PbF ₂ -UF ₄	5
		NaF-RbF-UF ₄	13
		RbF-ZrF ₄ -UF ₄	87, 95
		LiF-ZrF ₄ -UF ₄	93
		KF-ZrF ₄ -UF ₄	22, 94

Ternary Coolants		Corresponding Quaternary Fuels	
System	Mixtures	System	Mixtures
NaF-KF-LiF	12	NaF-KF-LiF-UF ₄	14, 106, 107
		NaF-KF-LiF-ThF ₄	23
NaF-KF-BeF ₂	6, 90	NaF-KF-BeF ₂ -UF ₄	15
NaF-KF-ZrF ₄	20, 24	NaF-KF-ZrF ₄ -UF ₄	19, 21, 25, 25a, 26, 110
NaF-LiF-ZrF ₄	73, 80, 81	NaF-LiF-ZrF ₄ -UF ₄	72, 82, 86, 91
NaF-LiF-BeF ₂	47, 78, 84, 88, 89, 96, 97	NaF-LiF-BeF ₂ -UF ₄	79, 85, 98
		NaF-RbF-BeF ₂ -UF ₄	109
		LiF-BeF ₂ -ThF ₄ -UF ₄	111

Binary Fuels	
System	Mixtures
NaF-UF ₄	37, 43
NaF-ThF ₄	48

TABULATED FLUORIDE PROPERTY DATA

Note: Mixture numbers 50 through 69 have been omitted. These numbers have been reserved by the ANP Chemistry Section for hydroxides (Ref. 1)

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
1	BeF ₂	12	7.50	75.2	514°C (957°F)
	NaF	76	42.41		
	UF ₄	12	50.09		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 3.77

LIQUID (ρ = gm/cc, T = °C) $\rho^* = 3.62 - 0.00075T$ (Ref. 3)

LIQUID (ρ = lbs/ft³, T = °F) $\rho^* = 226.8 - 0.0260T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10⁴) 2.42

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID (250° - 465°C)

Enthalpy (cal/gm) $H_T - H_0^{\circ C} = -5 + 0.219T$ (Ref. 4)

Heat Capacity (cal/gm °C) $c_p^* = 0.22$

Heat Capacity at 300°C (572°F) $c_p^* = 0.22$

LIQUID (520° - 990°C)

Enthalpy (cal/gm) $H_T - H_0^{\circ C} = -35 + 0.325T$

Heat Capacity (cal/gm °C) $c_p^* = 0.32$

Heat Capacity at 700°C (1292°F) $c_p^* = 0.32$

HEAT OF FUSION (cal/gm) $H_L - H_S = 24$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

°C	(Centipoises)	(Centistokes)	°F	(lb./ft-hr)	ft ² /hr
700	7.2* (Ref. 3)	2.33	1300	17.1*	0.0886
800	4.5*	1.50	1500	10.2*	0.0543

Exponential Form (centipoises)

[REDACTED] tes experimental values. Other values given are calculated or estimated.

<u>Mixture</u>	<u>Component</u>	<u>Mol %</u>	<u>Wt. %</u>	<u>Avg. M.W.</u>	<u>Liquidus Temp.</u>
2	NaF	46.5	16.14	121.0	530°C (986°F)
	KF	26.0	12.49		
	UF ₄	27.5	71.37		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 4.7* (Ref. 5)

LIQUID (ρ = gm/cc, T = °C) $\rho^* = 4.70 - 0.00115T$ (Ref. 6)

LIQUID (ρ = lbs/ft³, T = °F) $\rho^* = 294.7 - 0.0399T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C × 10⁴) 2.96

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID (240°-480°C)

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^* = -1 + 0.149T$ (Ref. 4)

Heat Capacity (cal/gm °C) $c_p^* = 0.15$

Heat Capacity at 300°C (572°F) $c_p^* = 0.15$

LIQUID (540°-1000°C)

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^* = -13 + 0.230T$

Heat Capacity (cal/gm °C) $c_p^* = 0.23$

Heat Capacity at 700°C (1292°F) $c_p^* = 0.23$

HEAT OF FUSION (cal/gm)

$H_L - H_S^* = 31$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F) 0.5 (Liquid) (Ref. 7)

VISCOSITY

<u>°C</u>	<u>(Centipoises)</u>	<u>(Centistokes)</u>	<u>°F</u>	<u>(lb./ft-hr)</u>	<u>ft²/hr</u>
600	17.3* (Ref. 8)	4.33	1100	43.6*	0.1768
700	9.8*	2.52	1300	23.5*	0.0983
800	6.3*	1.67	1500	14.3*	0.0616
900	4.35*	1.19			

Exponential Form (centipoises) $\mu = 0.0767e^{4731/T^{\circ}K}$

PRANDTL NUMBER 20 at 1100°F, 11 at 1300°F, 6.6 at 1500°F

*Denotes experimental values. Other values given are calculated or estimated.

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
2a	NaF	48.2	17.67	114.3	558°C (1036°F)
	KF	26.8	13.65		
	UF ₄	25.0	68.68		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc)	4.53
LIQUID (ρ = gm/cc, T = °C)	$\rho^* = 4.54 - 0.0011T$ (Ref. 15)
LIQUID (ρ = lbs/ft ³ , T = °F)	$\rho^* = 284.6 - 0.0381T$
MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10 ⁴)	2.92

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm)	$H_T - H_0$ °C * =
Heat Capacity (cal/gm °C)	$c_p^* =$
Heat Capacity at 300°C (572°F)	$c_p = 0.16$

LIQUID

Enthalpy (cal/gm)	$H_T - H_0$ °C * =
Heat Capacity (cal/gm °C)	$c_p^* =$
Heat Capacity at 700°C (1292°F)	$c_p = 0.23$

<u>HEAT OF FUSION (cal/gm)</u>	$H_L - H_S^* =$
--------------------------------	-----------------

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

°C	(Centipoises)	(Centistokes)	°F	(lb./ft-hr)	ft ² /hr
600	17.3		1100	43.6	
700	9.8		1300	23.5	
800	6.3		1500	14.3	
900	4.35				

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

<u>Mixture</u>	<u>Component</u>	<u>Mol %</u>	<u>Wt. %</u>	<u>Avg. M.W.</u>	<u>Liquidus Temp.</u>
3	BeF_2	60	32.87	85.8	465°C (869°F)
	NaF	25	12.23		
	UF_4	15	54.90		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 3.8^* (Ref. 5)

LIQUID (ρ = gm/cc, $T = {}^\circ\text{C}$) $\rho = 3.43 - 0.00070T$

LIQUID (ρ = lbs./ft.³, $T = {}^\circ\text{F}$) $\rho = 209.5 - 0.0243T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION ($1/{}^\circ\text{C} \times 10^4$) 2.37

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm) $H_T - H_0 {}^\circ\text{C}^* =$

Heat Capacity (cal/gm ${}^\circ\text{C}$) $c_p^* =$

Heat Capacity at 300°C (572°F) $c_p =$

LIQUID OR GLASS ($280^\circ\text{-}1050^\circ\text{C}$)

Enthalpy (cal/gm) $H_T - H_0 {}^\circ\text{C}^* = -43 + 0.315T$ (Ref. 4)

Heat Capacity (cal/gm ${}^\circ\text{C}$) $c_p^* = 0.32$

Heat Capacity at 700°C (1292°F) $c_p^* = 0.32$

HEAT OF FUSION (cal/gm) $H_L - H_S^* = 0$

THERMAL CONDUCTIVITY

K (BTU/hr ft ${}^\circ\text{F}$)

VISCOSITY

<u>${}^\circ\text{C}$</u>	<u>(Centipoises)</u>	<u>(Centistokes)</u>	<u>${}^\circ\text{F}$</u>	<u>(lb./ft-hr)</u>	<u>ft^2/hr</u>
--------------------------------------	----------------------	----------------------	--------------------------------------	--------------------	---

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
4	NaF	35	8.77	167.6	708°C (1306°F)
	KF	20	6.93		
	UF ₄	45	84.30		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 5.40

LIQUID (ρ = gm/cc, T = °C) $\rho = 5.60 - 0.00116T$

LIQUID (ρ = lbs/ft³, T = °F) $\rho = 350.9 - 0.0402T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION ($1/°C \times 10^4$) 2.44

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^*$ =

Heat Capacity (cal/gm °C) c_p^* =

Heat Capacity at 300°C (572°F) c_p = 0.14

LIQUID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^*$ =

Heat Capacity (cal/gm °C) c_p^* =

Heat Capacity at 700°C (1292°F) c_p =

HEAT OF FUSION (cal/gm) $H_L - H_S^*$ =

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

<u>°C</u>	<u>(Centipoises)</u>	<u>(Centistokes)</u>	<u>°F</u>	<u>(lb./ft-hr)</u>	<u>ft²/hr</u>
-----------	----------------------	----------------------	-----------	--------------------	--------------------------

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
5	NaF	60	18.67	135	465°C (869°F)
	PbF ₂	23	41.78		
	UF ₄	17	39.55		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 5.9* (Ref. 5)

LIQUID (ρ = gm/cc, T = °C) $\rho = 6.01 - 0.00122T$

LIQUID (ρ = lbs/ft³, T = °F) $\rho = 376.5 - 0.0423T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C $\times 10^4$) 2.35

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm) $H_T - H_0^{\circ C} * =$

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 300°C (572°F) $c_p = 0.14$

LIQUID

Enthalpy (cal/gm) $H_T - H_0^{\circ C} * =$

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 700°C (1292°F) $c_p = 0.19$

HEAT OF FUSION (cal/gm) $H_L - H_S^* =$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

$^{\circ}C$	(Centipoises)	(Centistokes)	$^{\circ}F$	(lb./ft-hr)	ft^2/hr
-------------	---------------	---------------	-------------	-------------	-----------

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
6	NaF	30	27.35	46.1	435°C (815°F)
	BeF ₂	65	66.33		
	KF	5	6.32		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 2.3* (Ref. 5)

LIQUID (ρ = gm/cc, T = °C) $\rho = 2.12 - 0.00033T$

LIQUID (ρ = lbs/ft³, T = °F) $\rho = 132.7 - 0.0114T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10⁴) 1.74

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm) $H_T - H_0^{\circ C} * =$

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 300°C (572°F) $c_p = 0.39$

LIQUID

Enthalpy (cal/gm) $H_T - H_0^{\circ C} * =$

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 700°C (1292°F) $c_p = 0.54$

HEAT OF FUSION (cal/gm) $H_L - H_S^* =$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

°C (Centipoises) (Centistokes) °F (lb./ft-hr) ft²/hr

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

<u>Mixture</u>	<u>Component</u>	<u>Mol %</u>	<u>Wt. %</u>	<u>Avg. M.W.</u>	<u>Liquidus Temp.</u>
7	NaF	50	16.55	126.8	575°C (1067°F)
	KF	20	9.16		
	UF ₄	30	74.28		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 5.1* (Ref. 5)

LIQUID (ρ = gm/cc, T = °C) $\rho = 4.78 - 0.00104T$

LIQUID (ρ = lbs/ft³, T = °F) $\rho = 299.5 - 0.0361T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10⁴) 2.57

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm) $H_T - H_0^{\circ C} * =$

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 300°C (572°F) $c_p = 0.15$

LIQUID

Enthalpy (cal/gm) $H_T - H_0^{\circ C} * =$

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 700°C (1292°F) $c_p = 0.22$

HEAT OF FUSION (cal/gm) $H_L - H_S^* =$

Thermal Conductivity

K (BTU/hr ft °F)

VISCOSITY

<u>°C</u>	<u>(Centipoises)</u>	<u>(Centistokes)</u>	<u>°F</u>	<u>(lb./ft-hr)</u>	<u>ft²/hr</u>
700	10.0		1300	23.7	
800	6.65		1500	15.3	
900	4.75				

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
8	NaF	100	100	42	995°C (1823°F)

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 2.79* (Ref. 9)

LIQUID (ρ = gm/cc, T = °C)

LIQUID (ρ = lbs/ft³, T = °F)

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION ($1/°C \times 10^4$)

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID (25° - 992°C)

$$H_T - H_0 = 0.2593T + 5.36 \times 10^{-5}T^2 \quad (\text{Ref. 46})$$

$$c_p^* = 0.2593 + 10.72 \times 10^{-5}T$$

$$c_p^* = 0.291$$

LIQUID (992° - 1027°C)

$$H_T - H_0 = 117.24 + 0.3810T$$

$$c_p^* = 0.381$$

$$c_p^* =$$

HEAT OF FUSION (cal/gm)

$$H_L - H_S^* = 185.2$$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

°C	(Centipoises)	(Centistokes)	°F	(lb./ft-hr)	ft²/hr
----	---------------	---------------	----	-------------	--------

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

<u>Mixture</u>	<u>Component</u>	<u>Mol %</u>	<u>Wt. %</u>	<u>Avg. M.W.</u>	<u>Liquidus Temp.</u>
9	BeF_2	100	100	47	543°C (1009°F)

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 1.98* (Ref. 9, 10)

LIQUID (ρ = gm/cc, T = °C)

LIQUID ($\rho = \text{lbs}/\text{ft}^3$, $T = {}^\circ\text{F}$)

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION ($1/\text{ }^{\circ}\text{C} \times 10^4$)

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLD

Heat Capacity (cal/gm °C)

Heat Capacity at 300°C (572°F) $c_p =$

LIQUID

Heat Capacity (cal/gm °C) C * =

Heat Capacity at 700°C (1292°F)

HEAT OF FUSION (cal/gm)

$$H_1 - H_2 \approx 0$$

THERMAL CONDUCTIVITY

K (BTU/hr ft $^{\circ}$ F)

VISCOSITY

$\frac{^{\circ}\text{C}}{\text{C}}$ (Centipoises) (Centistokes) ${}^{\circ}\text{F}$ (lb./ft.-hr) ft^2/hr

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

<u>Mixture</u>	<u>Composition</u>	<u>Mol %</u>	<u>Wt. %</u>	<u>Avg. M.W.</u>	<u>Liquidus Temp.</u>
10	LiF	100	100	25.9	848°C (1558°F)

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 2.64*(Ref. 9)

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID (0°-848°C)

Enthalpy (cal/gm)

$$H_T - H_{O^{\circ}C}^* = 0.54240T + 2.0624 \times 10^{-5} T^2 \\ - 2.4217 \times 10^{-8} T^3 + 0.40261 \times 10^{-10} T^4 \\ - 108.00 \log_{10}(T + 273.16/273.16)$$

(Ref. 47)

Heat Capacity (cal/gm °C)

$$c_p^* = 0.371 \text{ at } 0^{\circ}C \\ = 0.450 \text{ at } 200^{\circ}C \\ = 0.488 \text{ at } 400^{\circ}C \\ = 0.522 \text{ at } 600^{\circ}C \\ = 0.568 \text{ at } 800^{\circ}C$$

LIQUID (848°-900°C)

Enthalpy (cal/gm)

$$H_T - H_{O^{\circ}C}^* = 157.14 + 0.59777T$$

Heat Capacity (cal/gm °C)

$$c_p^* = 0.598$$

HEAT OF FUSION (cal/gm)

$$H_L - H_S^* = 249.4$$

*Denotes experimental values. Other values given are calculated or estimated.

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
11	KF	100	100	58.1	856°C (1573°F)

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 2.51* (Ref. 9)

LIQUID (ρ = gm/cc, T = °C)

LIQUID (ρ = lbs/ft³, T = °F)

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION ($1/°C \times 10^4$)

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID (25°-857°C)

$$H_T - H_0 = 0.2044T + 2.69 \times 10^{-5}T^2 \quad (\text{Ref. 46})$$

$$c_p^* = 0.2044 + 5.38 \times 10^{-5}T$$

$$c_p = 0.221$$

LIQUID (857°-927°C)

$$H_T - H_0 = 75.02 + 0.2754T$$

$$c_p^* = 0.2754$$

$$c_p =$$

HEAT OF FUSION (cal/gm)

$$H_L - H_S = 116.1$$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

°C	(Centipoises)	(Centistokes)	°F	(lb./ft-hr)	ft²/hr
----	---------------	---------------	----	-------------	--------

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
12	NaF	11.5	11.70	41.2	454°C (849°F)
	KF	42.0	59.09		
	LiF	46.5	29.21		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc)

2.6* (Ref. 5)

LIQUID (ρ = gm/cc, T = °C)

$\rho^* = 2.53 - 0.00073T$ (Ref. 16)

LIQUID (ρ = lbs/ft³, T = °F)

$\rho^* = 158.7 - 0.0253T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION ($1/°C \times 10^4$) 3.61

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID (60°-454°C)

$$H_T - H_0°C^* = -2.6 + 0.271T + 9.8 \times 10^{-5}T^2 \text{ (Ref. 4)}$$

$$c_p^* = 0.27 + 19.6 \times 10^{-5}T$$

$$c_p^* = 0.33$$

LIQUID (475°-875°C)

$$H_T - H_0°C^* = 30.3 + 0.453T$$

$$c_p^* = 0.45$$

$$c_p^* = 0.45$$

HEAT OF FUSION (cal/gm)

$$H_L - H_S^* = 95$$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

2.6 (Liquid) (Ref. 11)

2.7 (Solid sphere) (Ref. 45)

VISCOSITY

°C	(Centipoises)	(Centistokes)	°F	(lb./ft-hr)	ft²/hr
500	9.2* (Ref. 12)	4.26	1100	12.1*	0.0923
600	4.75*	2.27	1300	6.9*	0.0547
700	2.9*	1.44	1500	4.4*	0.0363
800	1.95*	1.00			

$$\text{Exponential Form (centipoises)} \quad \mu = 0.0400e^{4170/T^K}$$

PRANDTL NUMBER 2.1 at 1100°F, 1.2 at 1300°F, 0.76 at 1500°F

ELECTRICAL CONDUCTIVITY (ohm-cm)⁻¹ 1.34 at 1100°F, 1.58 at 1300°F, 1.80 at 1500°F
(Ref. 13)

*Denotes experimental values. Other values given are calculated or estimated.

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
13	NaF	53	17.40	128	490°C (914°F)
	RbF	20	16.33		
	UF ₄	27	66.27		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 5.02

LIQUID (ρ = gm/cc, T = °C) $\rho = 5.05 - 0.00108T$

LIQUID (ρ = lbs/ft³, T = °F) $\rho = 316.4 - 0.0374T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10⁴) 2.53

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^*$ =

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 300°C (572°F) $c_p = 0.15$

LIQUID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^*$ =

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 700°C (1292°F) $c_p = 0.21$

HEAT OF FUSION (cal/gm) $H_L - H_S^* =$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

°C	(Centipoises)	(Centistokes)	°F	(lb./ft-hr)	ft ² /hr
----	---------------	---------------	----	-------------	---------------------

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
14	NaF	10.9	10.21	44.9	452°C (846°F)
	KF	43.5	56.34		
	LiF	44.5	25.73		
	UF ₄	1.1	7.71		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 2.7* (Ref. 5)

LIQUID (ρ = gm/cc, T = °C) $\rho^* = 2.65 - 0.00090T$ (Ref. 17)

LIQUID (ρ = lbs/ft³, T = °F) $\rho^* = 166.4 - 0.0312T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C $\times 10^4$) 4.46

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID (90°-450°C)

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^*$ = $-9 + 0.310T$ (Ref. 4)

Heat Capacity (cal/gm °C) $c_p^* = 0.31$

Heat Capacity at 300°C (572°F) $c_p^* = 0.31$

LIQUID (500°-1000°C)

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^*$ = $21 + 0.437T$

Heat Capacity (cal/gm °C) $c_p^* = 0.44$

Heat Capacity at 700°C (1292°F) $c_p^* = 0.44$

HEAT OF FUSION (cal/gm)

$H_L - H_S^* = 87$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F) 2.3 (Liquid) (Ref. 14)
2.0 (Solid sphere) (Ref. 45)

VISCOSITY

°C	(Centipoises)	(Centistokes)	°F	(lb./ft-hr)	ft ² /hr
500	8.8* (Ref. 12)	4.00	1100	11.6*	0.0876
600	4.6*	2.18	1300	6.6*	0.0525
700	2.75*	1.36	1500	4.2*	0.0351
800	1.85*	0.96			

Exponential Form (centipoises) $\mu = 0.0348e^{4265/T^{\circ}K}$

PRANDTL NUMBER 2.2 at 1100°F; 1.3 at 1300°F, 0.80 at 1500°F

*Denotes experimental values. Other values given are calculated or estimated.

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
15	NaF	29.5	24.60	50.3	433°C (811°F)
	BeF ₂	64.0	59.75		
	KF	4.9	5.66		
	UF ₄	1.6	9.99		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 2.5* (Ref. 5)

LIQUID (ρ = gm/cc, T = °C) $\rho = 2.26 - 0.00036T$

LIQUID (ρ = lbs/ft³, T = °F) $\rho = 141.5 - 0.0125T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10⁴) 1.80

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^* =$

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 300°C (572°F) $c_p = 0.36$

LIQUID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^* =$

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 700°C (1292°F) $c_p = 0.51$

HEAT OF FUSION (cal/gm) $H_L - H_S^* =$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

°C	(Centipoises)	(Centistokes)	°F	(lb./ft-hr)	ft ² /hr
----	---------------	---------------	----	-------------	---------------------

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
16	NaF	34.0	21.00	68.0	550°C (1022°F)
	BeF ₂	57.5	39.74		
	UF ₄	8.5	39.26		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc)

2.99

LIQUID (ρ = gm/cc, T = °C)

$$\rho = 2.90 - 0.00054T$$

LIQUID (ρ = lbs/ft³, T = °F)

$$\rho = 181.6 - 0.0187T$$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C \times 10⁴) 2.14

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm) $H_T - H_0$ °C * =

Heat Capacity (cal/gm °C) c_p^* =

Heat Capacity at 300°C (572°F) c_p = 0.28

LIQUID

Enthalpy (cal/gm) $H_T - H_0$ °C * =

Heat Capacity (cal/gm °C) c_p^* =

Heat Capacity at 700°C (1292°F) c_p = 0.39

HEAT OF FUSION (cal/gm) $H_L - H_S$ * =

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

°C	(Centipoises)	(Centistokes)	°F	(lb./ft-hr)	ft ² /hr
----	---------------	---------------	----	-------------	---------------------

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
17	NaF	47	39.48	50.0	395°C (743°F)
	BeF ₂	51	47.96		
	UF ₄	2	12.56		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 2.6* (Ref. 5)

LIQUID (ρ = gm/cc, T = °C) $\rho = 2.39 - 0.00040T$

LIQUID (ρ = lbs./ft.³, T = °F) $\rho = 149.6 - 0.0139T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10⁴) 1.89

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C$ * =

Heat Capacity (cal/gm °C) c_p^* =

Heat Capacity at 300°C (572°F) c_p = 0.35

LIQUID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C$ * =

Heat Capacity (cal/gm °C) c_p^* =

Heat Capacity at 700°C (1292°F) c_p = 0.49

HEAT OF FUSION (cal/gm) $H_L - H_S$ * =

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

°C	(Centipoises)	(Centistokes)	°F	(lb./ft-hr)	ft ² /hr
600	16.5		1100	42.4	
700	8.0		1300	18.9	
800	4.4		1500	9.8	

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

<u>Mixture</u>	<u>Component</u>	<u>Mol %</u>	<u>Wt. %</u>	<u>Avg. M.W.</u>	<u>Liquidus Temp.</u>
18	NaF	45	19.57	96.5	506°C (943°F)
	LiF	33	8.87		
	UF ₄	22	71.56		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 5.0* (Ref, 5)

LIQUID (ρ = gm/cc, T = °C) $\rho = 4.54 - 0.00101T$

LIQUID (ρ = lbs/ft³, T = °F) $\rho = 284.5 - 0.035T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C $\times 10^4$) 2.64

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^* =$

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 300°C (572°F) $c_p = 0.19$

LIQUID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^* =$

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 700°C (1292°F) $c_p = 0.26$

HEAT OF FUSION (cal/gm) $H_L - H_S^* =$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

<u>°C</u>	<u>(Centipoises)</u>	<u>(Centistokes)</u>	<u>°F</u>	<u>(lb./ft-hr)</u>	<u>ft²/hr</u>
-----------	----------------------	----------------------	-----------	--------------------	--------------------------

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

<u>Mixture</u>	<u>Component</u>	<u>Mol %</u>	<u>Wt. %</u>	<u>Avg. M.W.</u>	<u>Liquidus Temp.</u>
19	NaF	5	1.94	108.2	405°C (761°F)
	KF	51	27.38		
	ZrF ₄	42	64.88		
	UF ₄	2	5.80		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc)	3.67
LIQUID (ρ = gm/cc, T = $^{\circ}$ C)	$\rho^* = 3.78 - 0.00109T$ (Ref. 18)
LIQUID (ρ = lbs/ft ³ , T = $^{\circ}$ F)	$\rho^* = 237.2 - 0.0378T$
MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/ $^{\circ}$ C x 10 ⁴)	3.48 (600 $^{\circ}$ C)

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm)	$H_T - H_0^{\circ}C^*$ =
Heat Capacity (cal/gm $^{\circ}C$)	c_p^* =
Heat Capacity at $300^{\circ}C$ ($572^{\circ}F$)	c_p = 0.18

LIQUID

Enthalpy (cal/gm)	$H_T - H_0^{\circ}C$	*
Heat Capacity (cal/gm $^{\circ}C$)	c_p^*	=
Heat Capacity at $700^{\circ}C$ ($1292^{\circ}F$)	c_p	= 0.25

HEAT OF FUSION (cal/gm) $H_L - H_S^* =$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

<u>°C</u>	<u>(Centipoises)</u>	<u>(Centistokes)</u>	<u>°F</u>	<u>(lb./ft-hr)</u>	<u>ft²/hr</u>
500	11.0		1100	16.0	
600	6.4		1300	10.3	
700	4.3		1500	7.6	
800	3.25				

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
20	NaF	5	2.01	104.2	425°C (797°F)
	KF	52	28.99		
	ZrF ₄	43	69.00		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 3.57
LIQUID (ρ = gm/cc, T = °C) $\rho = 3.38 - 0.00084T$
LIQUID (ρ = lbs/ft³, T = °F) $\rho = 211.9 - 0.0291T$
MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10⁴) 3.02

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm) $H_T - H_0^{\circ}\text{C}^* =$
Heat Capacity (cal/gm °C) $c_p^* =$
Heat Capacity at 300°C (572°F) $c_p = 0.19$

LIQUID

Enthalpy (cal/gm) $H_T - H_0^{\circ}\text{C}^* =$
Heat Capacity (cal/gm °C) $c_p^* =$
Heat Capacity at 700°C (1292°F) $c_p = 0.26$

HEAT OF FUSION (cal/gm) $H_L - H_S^* =$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

°C	(Centipoises)	(Centistokes)	°F	(lb./ft-hr)	ft ² /hr
500	10.5* (Ref. 19)	3.57	1100	15.2*	0.0850
600	6.1*	2.13	1300	9.8*	0.0566
700	4.1*	1.47	1500	7.1*	0.0424
800	3.1*	1.15			

Exponential Form (centipoises) $\mu = 0.161e^{3171/T^{\circ}\text{K}}$

*Denotes experimental values. Other values given are calculated or estimated.

<u>Mixture</u>	<u>Component</u>	<u>Mol %</u>	<u>Wt. %</u>	<u>Avg. M.W.</u>	<u>Liquidus Temp.</u>
21	NaF	4.8	1.80	112.1	540°C (1004°F)
	KF	50.1	25.96		
	ZrF ₄	41.3	61.59		
	UF ₄	3.8	10.65		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 3.76

LIQUID (ρ = gm/cc, T = °C) $\rho^* = 4.27 - 0.00163T$ (Ref. 18)

LIQUID (ρ = lbs/ft³, T = °F) $\rho^* = 268.3 - 0.0565T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C $\times 10^4$) 5.51 (800°C)

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

$$\begin{aligned} \text{Enthalpy (cal/gm)} & H_T - H_0^{\circ C} = \\ \text{Heat Capacity (cal/gm }^{\circ}\text{C)} & c_p^* = \\ \text{Heat Capacity at } 300^{\circ}\text{C (572°F)} & c_p = \end{aligned}$$

LIQUID (510°C-890°C)**

$$\begin{aligned} \text{Enthalpy (cal/gm)} & H_T - H_0^{\circ C} = -14.5 + 0.277T \text{ (Ref. 4)} \\ \text{Heat Capacity (cal/gm }^{\circ}\text{C)} & c_p^* = 0.28 \\ \text{Heat Capacity at } 700^{\circ}\text{C (1292°F)} & c_p = 0.28 \end{aligned}$$

$$\text{HEAT OF FUSION (cal/gm)} \quad H_L - H_S^* =$$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

<u>°C</u>	<u>(Centipoises)</u>	<u>(Centistokes)</u>	<u>°F</u>	<u>(lb./ft-hr)</u>	<u>ft²/hr</u>
600	6.7		1100	16.9	
700	4.5		1300	10.8	
800	3.4		1500	8.0	

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

**Discontinuity was noted in the temperature-enthalpy relationship in this temperature range.

<u>Mixture</u>	<u>Component</u>	<u>Mol %</u>	<u>Wt. %</u>	<u>Avg. M.W.</u>	<u>Liquidus Temp.</u>
22	KF	46	21.75	122.9	605°C (1121°F)
	ZrF ₄	50	68.03		
	UF ₄	4	10.22		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 3.90

LIQUID (ρ = gm/cc, T = °C) $\rho = 3.69 - 0.00089T$

LIQUID (ρ = lbs/ft³, T = °F) $\rho = 231.3 - 0.0309T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10⁴) 2.91

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^*$ =

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 300°C (572°F) $c_p = 0.17$

LIQUID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^*$ =

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 700°C (1292°F) $c_p = 0.24$

HEAT OF FUSION (cal/gm) $H_L - H_S^* =$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

°C (Centipoises) (Centistokes) °F (lb./ft-hr) ft²/hr

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
23	KF	41.8	56.61	42.9	450°C (842°F)
	NaF	11.4	11.16		
	LiF	46.2	27.92		
	ThF ₄	0.6	4.31		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 2.53

LIQUID (ρ = gm/cc, T = °C) $\rho = 2.52 - 0.00070T$

LIQUID (ρ = lbs/ft³, T = °F) $\rho = 158.1 - 0.0243T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10⁴) 3.45

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C$ * =

Heat Capacity (cal/gm °C) c_p^* =

Heat Capacity at 300°C (572°F) $c_p = 0.32$

LIQUID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C$ * =

Heat Capacity (cal/gm °C) c_p^* =

Heat Capacity at 700°C (1292°F) $c_p = 0.45$

HEAT OF FUSION (cal/gm) $H_L - H_S$ * =

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

°C	(Centipoises)	(Centistokes)	°F	(lb./ft-hr)	ft ² /hr
500	9.2		1100	12.1	
600	4.75		1300	6.9	
700	2.9		1500	4.4	
800	1.95				

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
24	KF	18	10.20	102.5	450°C (842°F)
	NaF	36	14.75		
	ZrF ₄	46	75.04		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 3.80

LIQUID (ρ = gm/cc, T = °C) $\rho = 3.59 - 0.00087T$

LIQUID (ρ = lbs/ft³, T = °F) $\rho = 225.1 - 0.0302T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10⁴) 2.92

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C * =$

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 300°C (572°F) $c_p = 0.19$

LIQUID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C * =$

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 700°C (1292°F) $c_p = 0.27$

HEAT OF FUSION (cal/gm) $H_L - H_S^* =$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

°C	(Centipoises)	(Centistokes)	°F	(lb./ft-hr)	ft ² /hr
600	7.15		1100	17.9	
700	4.4		1300	10.5	
800	3.05		1500	6.9	

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
25	KF	17.4	9.20	109.9	545°C (1013°F)
	NaF	34.7	13.25		
	ZrF ₄	44.4	67.55		
	UF ₄	3.5	10.00		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 3.97

LIQUID (ρ = gm/cc, T = °C) $\rho^* = 3.78 - 0.00091T$ (Ref. 18)

LIQUID (ρ = lbs/ft³, T = °F) $\rho^* = 237.0 - 0.0315T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10⁴) 2.90

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm) $H_T - H_0$ °C * =

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 300°C (572°F) $c_p = 0.18$

LIQUID

Enthalpy (cal/gm) $H_T - H_0$ °C * =

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 700°C (1292°F) $c_p = 0.25$

HEAT OF FUSION (cal/gm) $H_L - H_S^* =$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

°C	(Centipoises)	(Centistokes)	°F	(lb./ft-hr)	ft ² /hr
600	8.1		1100	20.3	
700	5.2		1300	12.1	
800	3.6		1500	8.0	

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

<u>Mixture</u>	<u>Component</u>	<u>Mol %</u>	<u>Wt. %</u>	<u>Avg. M.W.</u>	<u>Liquidus Temp.</u>
25a	KF	17.6	13.65	107.7	545°C (1015°F)
	NaF	35.1	9.47		
	ZrF ₄	44.8	69.55		
	UF ₄	2.5	7.34		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc)	3.92
LIQUID (ρ = gm/cc, T = °C)	$\rho^* = 3.65 - 0.00080T$ (Ref. 18)
LIQUID (ρ = lbs/ft ³ , T = °F)	$\rho^* = 228.7 - 0.0277T$
MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10 ⁴)	2.59

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm)	$H_T - H_0$ °C * =
Heat Capacity (cal/gm °C)	$c_p^* =$
Heat Capacity at 300°C (572°F)	$c_p = 0.19$

LIQUID

Enthalpy (cal/gm)	$H_T - H_0$ °C * =
Heat Capacity (cal/gm °C)	$c_p^* =$
Heat Capacity at 700°C (1292°F)	$c_p = 0.26$

<u>HEAT OF FUSION (cal/gm)</u>	$H_L - H_S^* =$
--------------------------------	-----------------

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

<u>°C</u>	<u>(Centipoises)</u>	<u>(Centistokes)</u>	<u>°F</u>	<u>(lb./ft-hr)</u>	<u>ft²/hr</u>
600	8.1		1100	20.3	
700	5.1		1300	12.1	
800	3.5		1500	8.0	

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

<u>Mixture</u>	<u>Component</u>	<u>Mol %</u>	<u>Wt. %</u>	<u>Avg. M.W.</u>	<u>Liquidus Temp.</u>
26	KF	14.0	7.28	111.6	540°C (1004°F)
	NaF	36.6	13.76		
	ZrF ₄	45.6	68.27		
	UF ₄	3.8	10.69		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 4.02

LIQUID (ρ = gm/cc, T = °C) $\rho = 3.82 - 0.00091T$

LIQUID (ρ = lbs/ft³, T = °F) $\rho = 239.5 - 0.0315T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10⁴) 2.87

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^* =$

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 300°C (572°F) $c_p = 0.18$

LIQUID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^* =$

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 700°C (1292°F) $c_p = 0.25$

HEAT OF FUSION (cal/gm) $H_L - H_S^* =$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

<u>°C</u>	<u>(Centipoises)</u>	<u>(Centistokes)</u>	<u>°F</u>	<u>(lb./ft-hr)</u>	<u>ft²/hr</u>
600	8.2		1100	20.6	
700	5.3		1300	12.6	
800	3.7		1500	8.5	

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

<u>Mixture</u>	<u>Component</u>	<u>Mol %</u>	<u>Wt. %</u>	<u>Avg. M.W.</u>	<u>Liquidus Temp.</u>
27	NaF	46	16.73	115.5	510°C (950°F)
	ZrF ₄	50	72.39		
	UF ₄	4	10.88		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 4.17

LIQUID (ρ = gm/cc, T = °C) $\rho = 3.97 - 0.00093T$

LIQUID (ρ = lbs/ft³, T = °F) $\rho = 248.9 - 0.0322T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10⁴) 2.79

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^*$ =

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 300°C (572°F) $c_p = 0.18$

LIQUID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^*$ =

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 700°C (1292°F) $c_p = 0.25$

HEAT OF FUSION (cal/gm) $H_L - H_S^* =$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F) 0.6 (solid sphere and slab)(Ref. 45)

VISCOSITY

<u>°C</u>	<u>(Centipoises)</u>	<u>(Centistokes)</u>	<u>°F</u>	<u>(lb./ft-hr)</u>	<u>ft²/hr</u>
600	8.9		1100	22.3	
700	5.7		1300	13.6	
800	3.9		1500	9.0	

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
28	NaF ZrF ₄	48 52	18.82 81.18	107.1	515°C (959°F)

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 3.99

LIQUID ($\rho = \text{gm/cc}$, $T = {}^\circ\text{C}$) $\rho = 3.79 - 0.00090T$

LIQUID ($\rho = \text{lbs}/\text{ft}^3$, $T = {}^\circ\text{F}$) $\rho = 237.6 - 0.0312T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION ($1/{}^\circ\text{C} \times 10^4$) 2.86

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm) $H_T - H_0 {}^\circ\text{C}^* =$

Heat Capacity (cal/gm ${}^\circ\text{C}$) $c_p^* =$

Heat Capacity at 300°C (572°F) $c_p = 0.19$

LIQUID

Enthalpy (cal/gm) $H_T - H_0 {}^\circ\text{C}^* =$

Heat Capacity (cal/gm ${}^\circ\text{C}$) $c_p^* =$

Heat Capacity at 700°C (1292°F) $c_p = 0.27$

HEAT OF FUSION (cal/gm) $H_L - H_S^* =$

THERMAL CONDUCTIVITY

K (BTU/hr ft ${}^\circ\text{F}$)

VISCOSITY

${}^\circ\text{C}$	(Centipoises)	(Centistokes)	${}^\circ\text{F}$	(lb./ft-hr)	ft^2/hr
600	8.5		1100	21.5	
700	5.3		1300	12.5	
800	3.5		1500	8.0	

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

<u>Mixture</u>	<u>Component</u>	<u>Mol %</u>	<u>Wt. %</u>	<u>Avg. M.W.</u>	<u>Liquidus Temp.</u>
29	NaF	42.2	15.49	114.3	570°C (1058°F)
	ZrF ₄	57.8	84.51		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 4.06

LIQUID (ρ = gm/cc, T = °C) $\rho = 3.86 - 0.00092T$

LIQUID (ρ = lbs/ft³, T = °F) $\rho = 242.0 - 0.0319T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10⁴) 2.87

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm) $H_T - H_0^{\circ C} * =$

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 300°C (572°F) $c_p = 0.19$

LIQUID

Enthalpy (cal/gm) $H_T - H_0^{\circ C} * =$

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 700°C (1292°F) $c_p = 0.26$

HEAT OF FUSION (cal/gm) $H_L - H_S^* =$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

<u>°C</u>	<u>(Centipoises)</u>	<u>(Centistokes)</u>	<u>°F</u>	<u>(lb./ft-hr)</u>	<u>ft²/hr</u>
-----------	----------------------	----------------------	-----------	--------------------	--------------------------

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
30	NaF	50	19.01	110.5	520°C (968°F)
	ZrF ₄	46	69.62		
	UF ₄	4	11.37		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 4.09* (Ref. 10)

LIQUID (ρ = gm/cc, T = °C) $\rho = 3.93 - 0.00093T$

LIQUID (ρ = lbs/ft³, T = °F) $\rho = 246.4 - 0.0322T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10⁴) 2.84

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID (340°-500°C)

Enthalpy (cal/gm) $H_T - H_0^{\circ C} = -12.6 + 0.215T$ (Ref. 4)

Heat Capacity (cal/gm °C) $c_p^* = 0.22$

Heat Capacity at 300°C (572°F) $c_p^* = 0.22$

LIQUID (540°-894°C)

Enthalpy (cal/gm) $H_T - H_0^{\circ C} = 2.1 + 0.3178T - 4.28 \times 10^{-5}T^2$

Heat Capacity (cal/gm °C) $c_p^* = 0.3178 - 8.56 \times 10^{-5}T$

Heat Capacity at 700°C (1292°F) $c_p^* = 0.258$

HEAT OF FUSION (cal/gm)

$H_L - H_S = 57$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F) 0.5 (Solid slab) (Ref. 45)

1.3 (Liquid) (Ref. 14)

VISCOSITY

°C	(Centipoises)	(Centistokes)	°F	(lb./ft-hr)	ft ² /hr
600	8.5* (Ref. 20)	2.52	1100	21.3*	0.1009
700	5.4*	1.65	1300	12.8*	0.0625
800	3.7*	1.16	1500	8.5*	0.0430
850	3.2*	1.02			

Exponential Form (centipoises) $\mu = 0.0981e^{3895/T^{\circ K}}$

PRANDTL NUMBER 4.4 at 1100°F, 2.5 at 1300°F, 1.6 at 1500°F

ELECTRICAL CONDUCTIVITY (ohm-cm)⁻¹ 0.87 at 1100°F, 1.16 at 1300°F, 1.45 at 1500°F (Ref. 13)

SURFACE TENSION (dynes/cm) 157 at 530°C, 132 at 630°C, 115 at 730°C (Ref. 21)

*Denotes experimental values. Other values given are calculated or estimated.

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
31	NaF ZrF ₄	50 50	20.08 79.92	104.6	510°C (950°F)

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 4.11* (Ref. 22)

LIQUID (ρ = gm/cc, T = °C) $\rho^* = 3.79 - 0.00093T$ (Ref. 23)

LIQUID (ρ = lbs/ft³, T = °F) $\rho^* = 237.6 - 0.0322T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10⁴) 2.96

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID (54°-488°C)

$$\begin{aligned} \text{Enthalpy (cal/gm)} & H_T - H_0^{\circ C} = 0.1 + 0.1798T + 2.69 \times 10^{-5}T^2 \text{ (Ref. 4)} \\ \text{Heat Capacity (cal/gm }^{\circ}\text{C)} & c_p^* = 0.1798 + 5.38 \times 10^{-5}T \\ \text{Heat Capacity at } 300^{\circ}\text{C (572°F)} & c_p^* = 0.196 \end{aligned}$$

LIQUID (546°-899°C)

$$\begin{aligned} \text{Enthalpy (cal/gm)} & H_T - H_0^{\circ C} = -5.3 + 0.3508T - 5.39 \times 10^{-5}T^2 \\ \text{Heat Capacity (cal/gm }^{\circ}\text{C)} & c_p^* = 0.3508 - 10.79 \times 10^{-5}T \\ \text{Heat Capacity at } 700^{\circ}\text{C (1292°F)} & c_p^* = 0.275 \end{aligned}$$

HEAT OF FUSION (cal/gm)

$$H_L - H_S = 61$$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

°C	(Centipoises)	(Centistokes)	°F	(lb./ft-hr)	ft ² /hr
600	8.4* (Ref. 24)	2.60	1100	20.9*	0.1033
700	5.2*	1.66	1300	12.3*	0.0627
800	3.45*	1.13	1500	7.9*	0.0416

$$\text{Exponential Form (centipoises)} \quad \mu = 0.0709 e^{4168/T^{\circ}\text{K}}$$

ELECTRICAL CONDUCTIVITY (ohm-cm)⁻¹ 0.64 at 1100°F, 1.05 at 1300°F, 1.47 at 1500°F
(Ref. 13)

*Denotes experimental values. Other values given are calculated or estimated.

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
32	NaF ZrF ₄	52 48	21.39 78.61	102.1	515°C (959°F)

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 4.10*(Ref. 22)

LIQUID (ρ = gm/cc, T = °C) $\rho = 3.72 - 0.00089T$

LIQUID (ρ = lbs/ft³, T = °F) $\rho = 233.2 - 0.0309T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10⁴) 2.87

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm) $H_T - H_0^{\circ C} * =$

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 300°C (572°F) $c_p = 0.20$

LIQUID

Enthalpy (cal/gm) $H_T - H_0^{\circ C} * =$

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 700°C (1292°F) $c_p = 0.27$

HEAT OF FUSION (cal/gm) $H_L - H_S^* =$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

°C	(Centipoises)	(Centistokes)	°F	(lb./ft-hr)	ft ² /hr
600	7.9		1100	20.1	
700	4.8		1300	11.4	
800	3.35		1500	7.7	

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

<u>Mixture</u>	<u>Component</u>	<u>Mol %</u>	<u>Wt. %</u>	<u>Avg. M.W.</u>	<u>Liquidus Temp.</u>
33	NaF	50	14.86	141.4	610°C (1130°F)
	ZrF ₄	25	29.58		
	UF ₄	25	55.56		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 4.93
LIQUID (ρ = gm/cc, T = °C) $\rho^* = 5.09 - 0.00159T$ (Ref. 23)
LIQUID (ρ = lbs/ft³, T = °F) $\rho^* = 319.5 - 0.0551T$
MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION ($1/°C \times 10^4$) 3.99

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID (280°-610°C)

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^*$ = $-17.7 + 0.166T$ (Ref. 4)
Heat Capacity (cal/gm °C) $c_p^* = 0.17$
Heat Capacity at 300°C (572°F) $c_p^* = 0.17$

LIQUID (610°-930°C)

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^*$ = $-39.0 + 0.270T$
Heat Capacity (cal/gm °C) $c_p^* = 0.27$
Heat Capacity at 700°C (1292°F) $c_p^* = 0.27$

HEAT OF FUSION (cal/gm) $H_L - H_S^* = 42$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

<u>°C</u>	<u>(Centipoises)</u>	<u>(Centistokes)</u>	<u>°F</u>	<u>(lb./ft-hr)</u>	<u>ft²/hr</u>
700	8.5* (Ref. 25)	2.05	1300	20.1*	0.0781
800	5.0*	1.24	1500	11.3*	0.0451
900	3.5*	0.89			

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
34	NaF ZrF ₄	57 43	24.98 75.02	95.8	500°C (932°F)

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc)	3.86
LIQUID ($\rho = \text{gm/cc}$, $T = {}^\circ\text{C}$)	$\rho = 3.65 - 0.00088T$
LIQUID ($\rho = \text{lbs}/\text{ft}^3$, $T = {}^\circ\text{F}$)	$\rho = 228.8 - 0.0305T$
MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION ($1/{}^\circ\text{C} \times 10^4$)	2.90

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm)	$H_T - H_0 {}^\circ\text{C}^*$ =
Heat Capacity (cal/gm ${}^\circ\text{C}$)	$c_p^* =$
Heat Capacity at 300°C (572°F)	$c_p = 0.20$

LIQUID

Enthalpy (cal/gm)	$H_T - H_0 {}^\circ\text{C}^*$ =
Heat Capacity (cal/gm ${}^\circ\text{C}$)	$c_p^* =$
Heat Capacity at 700°C (1292°F)	$c_p = 0.28$

<u>HEAT OF FUSION (cal/gm)</u>	$H_L - H_S^* =$
--------------------------------	-----------------

THERMAL CONDUCTIVITY

K (BTU/hr ft ${}^\circ\text{F}$)

VISCOSITY

${}^\circ\text{C}$	(Centipoises)	(Centistokes)	${}^\circ\text{F}$	(lb./ft-hr)	ft^2/hr
600	7.5		1100	18.9	
700	4.6		1300	10.9	
800	3.2		1500	7.4	

Exponential Form (centipoises)

ELECTRICAL CONDUCTIVITY ($\text{ohm}\cdot\text{cm}$)⁻¹ 0.95 at 1100°F, 1.41 at 1300°F, 1.85 at 1500°F
(Ref. 13)

*Denotes experimental values. Other values given are calculated or estimated.

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
35	NaF	57	54.22	44.1	360°C (680°F)
	BeF ₂	43	45.78		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 2.35

LIQUID ($\rho = \text{gm/cc}$, $T = {}^\circ\text{C}$) $\rho = 2.27 - 0.00037T$

LIQUID ($\rho = \text{lbs}/\text{ft}^3$, $T = {}^\circ\text{F}$) $\rho = 142.1 - 0.0128T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION ($1/{}^\circ\text{C} \times 10^4$) 1.84

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm) $H_T - H_0 {}^\circ\text{C}^* =$

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 300°C (572°F) $c_p = 0.37$

LIQUID

Enthalpy (cal/gm) $H_T - H_0 {}^\circ\text{C}^* =$

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 700°C (1292°F) $c_p = 0.52$

HEAT OF FUSION (cal/gm) $H_L - H_S^* =$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F) 2.4 (Liquid) (Ref. 26)

VISCOSITY

°C	(Centipoises)	(Centistokes)	°F	(lb./ft-hr)	ft ² /hr
550	18.0 (Ref. 27)	8.70	1100	32.7*	0.2555
600	12.8*	6.27	1300	16.5*	0.1315
700	7.0*	3.43	1500	9.6*	0.0783
800	4.25*	2.16			

Exponential Form (centipoises) $\mu = 0.0346e^{5164/T_K}$

PRANDTL NUMBER 7.1 at 1100°F, 3.6 at 1300°F, 2.1 at 1500°F

*Denotes experimental values. Other values given are calculated or estimated.

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
36	NaF	55	40.10	57.6	450°C (842°F)
	BeF ₂	40	32.64		
	UF ₄	5	27.26		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 2.86

LIQUID (ρ = gm/cc, T = °C) $\rho = 2.76 - 0.00050T$

LIQUID (ρ = lbs/ft³, T = °F) $\rho = 172.8 - 0.0173T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10⁴) 2.08

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^*$ =

Heat Capacity (cal/gm °C) c_p^* =

Heat Capacity at 300°C (572°F) c_p = 0.30

LIQUID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^*$ =

Heat Capacity (cal/gm °C) c_p^* =

Heat Capacity at 700°C (1292°F) c_p = 0.42

HEAT OF FUSION (cal/gm) $H_L - H_S^*$ =

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

°C	(Centipoises)	(Centistokes)	°F	(lb./ft-hr)	ft ² /hr
600	11.2		1100	28.3	
700	5.6		1300	13.1	
800	3.2		1500	7.1	

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
37	NaF UF ₄	50 50	11.80 88.20	178.05	715°C (1319°F)

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 5.75
LIQUID (ρ = gm/cc, T = °C) $\rho = 6.16 - 0.00123T$
LIQUID (ρ = lbs/ft³, T = °F) $\rho = 385.9 - 0.0426T$
MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10⁴) 2.32

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^*$ =
Heat Capacity (cal/gm °C) $c_p^* =$
Heat Capacity at 300°C (572°F) $c_p = 0.13$

LIQUID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^*$ =
Heat Capacity (cal/gm °C) $c_p^* =$
Heat Capacity at 700°C (1292°F) $c_p =$

HEAT OF FUSION (cal/gm) $H_L - H_S^* =$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

<u>°C</u>	<u>(Centipoises)</u>	<u>(Centistokes)</u>	<u>°F</u>	<u>(lb./ft-hr)</u>	<u>ft²/hr</u>
-----------	----------------------	----------------------	-----------	--------------------	--------------------------

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

<u>Mixture</u>	<u>Component</u>	<u>Mol %</u>	<u>Wt. %</u>	<u>Avg. M.W.</u>	<u>Liquidus Temp.</u>
38	NaF	50	19.53	107.5	510°C (950°F)
	ZrF ₄	48	74.63		
	UF ₄	2	5.84		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 4.04

LIQUID (ρ = gm/cc, T = °C) $\rho = 3.83 - 0.00091T$

LIQUID (ρ = lbs/ft³, T = °F) $\rho = 240.1 - 0.0315T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10⁴) 2.84

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^* =$

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 300°C (572°F) $c_p = 0.19$

LIQUID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^* =$

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 700°C (1292°F) $c_p = 0.26$

HEAT OF FUSION (cal/gm) $H_L - H_S^* =$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

<u>°C</u>	<u>(Centipoises)</u>	<u>(Centistokes)</u>	<u>°F</u>	<u>(lb./ft-hr)</u>	<u>ft²/hr</u>
600	8.5		1100	21.3	
700	5.4		1300	12.8	
800	3.7		1500	8.5	

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

<u>Mixture</u>	<u>Component</u>	<u>Mol %</u>	<u>Wt. %</u>	<u>Avg. M.W.</u>	<u>Liquidus Temp.</u>
39	NaF	65	23.69	115.2	610°C (1130°F)
	ZrF ₄	15	21.80		
	UF ₄	20	54.51		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 4.64

LIQUID (ρ = gm/cc, T = °C) $\rho = 4.55 - 0.00102T$

LIQUID (ρ = lbs/ft³, T = °F) $\rho = 285.2 - 0.0354T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION ($1/°C \times 10^4$) 2.66

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID (90° - 610°C)

Enthalpy (cal/gm) $H_T - H_0 = -2.9 + 0.172T$ (Ref. 4)

Heat Capacity (cal/gm °C) $c_p^* = 0.17$

Heat Capacity at 300°C (572°F) $c_p^* = 0.17$

LIQUID (653° - 924°C)

Enthalpy (cal/gm) $H_T - H_0 = 22.3 + 0.199T$

Heat Capacity (cal/gm °C) $c_p^* = 0.20$

Heat Capacity at 700°C (1292°F) $c_p^* = 0.20$

HEAT OF FUSION (cal/gm) $H_L - H_S^* = 42$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

<u>°C</u>	<u>(Centipoises)</u>	<u>(Centistokes)</u>	<u>°F</u>	<u>(lb./ft-hr)</u>	<u>ft²/hr</u>
-----------	----------------------	----------------------	-----------	--------------------	--------------------------

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
40	NaF	53	20.83	106.8	520°C (968°F)
	ZrF ₄	43	67.42		
	UF ₄	4	11.75		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 4.09

LIQUID (ρ = gm/cc, T = °C) $\rho = 3.90 - 0.00092T$

LIQUID (ρ = lbs/ft³, T = °F) $\rho = 244.5 - 0.0319T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10⁴) 2.83

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID (70° - 520°C)

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^*$ = 0.0 + 0.182T (Ref. 4)

Heat Capacity (cal/gm °C) c_p^* = 0.18

Heat Capacity at 300°C (572°F) c_p^* = 0.18

LIQUID (571° - 884°C)

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^*$ = 19.4 + 0.2656T

Heat Capacity (cal/gm °C) c_p^* = 0.266

Heat Capacity at 700°C (1292°F) c_p^* = 0.266

HEAT OF FUSION (cal/gm)

$H_L - H_S^*$ = 63

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

°C	(Centipoises)	(Centistokes)	°F	(lb./ft-hr)	ft ² /hr
600	8.3		1100	20.8	
700	5.3		1300	12.6	
800	3.65		1500	8.4	

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
41	NaF	63	24.97	106.0	595°C (1103°F)
	ZrF ₄	25	39.45		
	UF ₄	12	35.57		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 4.32

LIQUID (ρ = gm/cc, T = °C) $\rho = 4.15 - 0.00096T$

LIQUID (ρ = lbs/ft³, T = °F) $\rho = 260.1 - 0.0333T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10⁴) 2.77

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^*$ =

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 300°C (572°F) $c_p = 0.17$

LIQUID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^*$ =

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 700°C (1292°F) $c_p = 0.24$

HEAT OF FUSION (cal/gm) $H_L - H_S^* =$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

°C	(Centipoises)	(Centistokes)	°F	(lb./ft-hr)	ft ² /hr
----	---------------	---------------	----	-------------	---------------------

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
42	NaF	64.5	20.87	129.8	650°C (1202°F)
	ZrF ₄	6.0	7.73		
	UF ₄	29.5	71.40		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 5.03

LIQUID (ρ = gm/cc, T = °C) $\rho = 5.05 - 0.00107T$

LIQUID (ρ = lbs/ft³, T = °F) $\rho = 316.4 - 0.0371T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10⁴) 2.49

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^*$ =

Heat Capacity (cal/gm °C) c_p^* =

Heat Capacity at 300°C (572°F) $c_p = 0.14$

LIQUID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^*$ =

Heat Capacity (cal/gm °C) c_p^* =

Heat Capacity at 700°C (1292°F) $c_p = 0.19$

HEAT OF FUSION (cal/gm) $H_L - H_S^*$ =

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

°C	(Centipoises)	(Centistokes)	°F	(lb./ft-hr)	ft ² /hr
700	10.25		1300	24.2	
800	7.0		1500	16.1	
900	5.15				

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

<u>Mixture</u>	<u>Component</u>	<u>Mol %</u>	<u>Wt. %</u>	<u>Avg. M.W.</u>	<u>Liquidus Temp.</u>
43	NaF UF ₄	66.7 33.3	21.12 78.88	132.6	665°C (1229°F)

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc)	5.17
LIQUID ($\rho = \text{gm/cc}$, $T = {}^\circ\text{C}$)	$\rho^* = 5.51 - 0.0013T$ (Ref. 16)
LIQUID ($\rho = \text{lbs}/\text{ft}^3$, $T = {}^\circ\text{F}$)	$\rho^* = 345.4 - 0.0451T$
MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION ($1/{}^\circ\text{C} \times 10^4$)	2.83

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm)	$H_T - H_0 {}^\circ\text{C}^*$ =
Heat Capacity (cal/gm ${}^\circ\text{C}$)	$c_p^* =$
Heat Capacity at $300 {}^\circ\text{C}$ (572°F)	$c_p = 0.15$

LIQUID

Enthalpy (cal/gm)	$H_T - H_0 {}^\circ\text{C}^*$ =
Heat Capacity (cal/gm ${}^\circ\text{C}$)	$c_p^* =$
Heat Capacity at $700 {}^\circ\text{C}$ (1292°F)	$c_p = 0.21$

<u>HEAT OF FUSION (cal/gm)</u>	$H_L - H_S^* =$
--------------------------------	-----------------

THERMAL CONDUCTIVITY

K (BTU/hr ft ${}^\circ\text{F}$)

VISCOSITY

<u>°C</u>	<u>(Centipoises)</u>	<u>(Centistokes)</u>	<u>°F</u>	<u>(lb./ft-hr)</u>	<u>ft²/hr</u>
700	10.25* (Ref. 28)	2.23	1300	24.2*	0.0843
800	7.0*	1.57	1500	16.1*	0.0580
900	5.15*	1.19			

$$\text{Exponential Form (centipoises)} \quad \mu = 0.181e^{3927/T^\circ\text{K}}$$

*Denotes experimental values. Other values given are calculated or estimated.

<u>Mixture</u>	<u>Component</u>	<u>Mol %</u>	<u>Wt. %</u>	<u>Avg. M.W.</u>	<u>Liquidus Temp.</u>
44	NaF	53.5	20.47	109.8	540°C (1004°F)
	ZrF ₄	40.0	60.93		
	UF ₄	6.5	18.60		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc)	4.19
LIQUID (ρ = gm/cc, T = °C)	$\rho^* = 4.04 - 0.0011T$ (Ref. 16)
LIQUID (ρ = lbs/ft ³ , T = °F)	$\rho^* = 253.4 - 0.0381T$
MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10 ⁴)	3.36

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID (260° - 490°C)

Enthalpy (cal/gm)	$H_T - H_0^o C^* = -4.1 + 0.189T$ (Ref. 4)
Heat Capacity (cal/gm °C)	$c_p^* = 0.19$
Heat Capacity at 300°C (572°F)	$c_p^* = 0.19$

LIQUID (590° - 920°C)

Enthalpy (cal/gm)	$H_T - H_0^o C^* = 34.5 + 0.235T$
Heat Capacity (cal/gm °C)	$c_p^* = 0.24$
Heat Capacity at 700°C (1292°F)	$c_p^* = 0.24$

HEAT OF FUSION (cal/gm)

$$H_L - H_S^* = 63$$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)	1.2 (Liquid) (Ref. 29)
------------------	------------------------

VISCOSITY

<u>°C</u>	<u>(Centipoises)</u>	<u>(Centistokes)</u>	<u>°F</u>	<u>(lb./ft-hr)</u>	<u>ft²/hr</u>
600	8.5* (Ref. 22)	2.51	1100	21.1*	0.0968
700	5.7*	1.74	1300	13.7*	0.0648
800	4.2*	1.33	1500	9.7*	0.0474
850	3.7*	1.14			

$$\text{Exponential Form (centipoises)} \quad \mu = 0.194e^{3302/T^{\circ K}}$$

PRANDTL NUMBER 4.2 at 1100°F, 2.7 at 1300°F, 1.9 at 1500°F

ELECTRICAL CONDUCTIVITY (ohm-cm)⁻¹ 0.66 at 1100°F, 0.97 at 1300°F, 1.27 at 1500°F
(Ref. 13)

*Denotes experimental values. Other values given are calculated or estimated.

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
45	NaF ZrF ₄	53 47	22.07 77.93	100.9	520°C (968°F)

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc)	4.11* (Ref. 22)
LIQUID (ρ = gm/cc, T = °C)	$\rho = 3.71 - 0.00089T$
LIQUID (ρ = lbs/ft ³ , T = °F)	$\rho = 232.6 - 0.0309T$
MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10 ⁴)	2.89

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm)	$H_T - H_0^{\circ C} * =$
Heat Capacity (cal/gm °C)	$c_p^* =$
Heat Capacity at 300°C (572°F)	$c_p = 0.20$

LIQUID

Enthalpy (cal/gm)	$H_T - H_0^{\circ C} * =$
Heat Capacity (cal/gm °C)	$c_p^* =$
Heat Capacity at 700°C (1292°F)	$c_p = 0.27$

HEAT OF FUSION (cal/gm) $H_L - H_S^* =$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

°C	(Centipoises)	(Centistokes)	°F	(lb./ft-hr)	ft ² /hr
600	7.5* (Ref. 22)	2.36	1100	18.9*	0.0952
700	4.6*	1.49	1300	10.9*	0.0567
800	3.2*	1.07	1500	7.4*	0.0398

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
C TEST	NaF ZrF ₄	66.7 33.3	33.47 66.53	83.7	680°C (1256°F)

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 3.70
LIQUID ($\rho = \text{gm/cc}$, $T = {}^\circ\text{C}$) $\rho = 3.49 - 0.00086T$
LIQUID ($\rho = \text{lbs}/\text{ft}^3$, $T = {}^\circ\text{F}$) $\rho = 218.8 - 0.0298T$
MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION ($1/{}^\circ\text{C} \times 10^4$) 2.53

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm) $H_T - H_0 {}^\circ\text{C}^* =$
Heat Capacity (cal/gm ${}^\circ\text{C}$) $c_p^* =$
Heat Capacity at $300 {}^\circ\text{C}$ (572°F) $c_p = 0.21$

LIQUID

Enthalpy (cal/gm) $H_T - H_0 {}^\circ\text{C}^* =$
Heat Capacity (cal/gm ${}^\circ\text{C}$) $c_p^* =$
Heat Capacity at $700 {}^\circ\text{C}$ (1292°F) $c_p = 0.29$

HEAT OF FUSION (cal/gm) $H_L - H_S^* =$

THERMAL CONDUCTIVITY

K (BTU/hr ft ${}^\circ\text{F}$)

VISCOSITY

${}^\circ\text{C}$	(Centipoises)	(Centistokes)	${}^\circ\text{F}$	(lb./ft-hr)	ft^2/hr
--------------------	---------------	---------------	--------------------	-------------	-------------------------

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
46	NaF	62.5	20.90	125.7	635°C (1175°F)
	ZrF ₄	12.5	16.61		
	UF ₄	25.0	62.49		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 4.86

LIQUID (ρ = gm/cc, T = °C) $\rho^* = 4.75 - 0.0012T$ (Ref. 16)

LIQUID (ρ = lbs/ft³, T = °F) $\rho^* = 266.6 - 0.0416T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10⁴) 3.07

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^*$ =

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 300°C (572°F) $c_p = 0.15$

LIQUID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^*$ =

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 700°C (1292°F) $c_p = 0.20$

HEAT OF FUSION (cal/gm) $H_L - H_S^* =$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

<u>°C</u>	<u>(Centipoises)</u>	<u>(Centistokes)</u>	<u>°F</u>	<u>(lb./ft-hr)</u>	<u>ft²/hr</u>
-----------	----------------------	----------------------	-----------	--------------------	--------------------------

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
47	NaF	35	16.75	41.1	335°C (635°F)
	LiF	20	59.13		
	BeF ₂	45	24.12		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc)	2.26
LIQUID (ρ = gm/cc, T = °C)	$\rho = 2.19 - 0.00035T$
LIQUID (ρ = lbs/ft ³ , T = °F)	$\rho = 137.1 - 0.0121T$
MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10 ⁴)	1.79

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm)	$H_T - H_0^{\circ}C$ * =
Heat Capacity (cal/gm °C)	c_p^* =
Heat Capacity at 300°C (572°F)	c_p = 0.40

LIQUID

Enthalpy (cal/gm)	$H_T - H_0^{\circ}C$ * =
Heat Capacity (cal/gm °C)	c_p^* =
Heat Capacity at 700°C (1292°F)	c_p = 0.56

<u>HEAT OF FUSION (cal/gm)</u>	$H_L - H_S$ * =
--------------------------------	-----------------

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

$^{\circ}C$ (Centipoises) (Centistokes) $^{\circ}F$ (lb./ft-hr) ft²/hr

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

<u>Mixture</u>	<u>Component</u>	<u>Mol %</u>	<u>Wt. %</u>	<u>Avg. M.W.</u>	<u>Liquidus Temp.</u>
48	NaF ThF ₄	50 50	12.00 88.00	175.1	733°C (1351°F)

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 5.73

LIQUID (ρ = gm/cc, T = °C) $\rho = 6.13 - 0.00123T$

LIQUID (ρ = lbs/ft³, T = °F) $\rho = 384.0 - 0.0426T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10⁴) 2.32

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm) $H_T - H_0°C^* =$

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 300°C (572°F) $c_p = 0.14$

LIQUID

Enthalpy (cal/gm) $H_T - H_0°C^* =$

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 700°C (1292°F) $c_p =$

HEAT OF FUSION (cal/gm) $H_L - H_S^* =$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

<u>°C</u>	<u>(Centipoises)</u>	<u>(Centistokes)</u>	<u>°F</u>	<u>(lb./ft-hr)</u>	<u>ft²/hr</u>
-----------	----------------------	----------------------	-----------	--------------------	--------------------------

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
49	NaF	40	13.85	121.0	510°C (950°F)
	ZrF ₄	57	78.85		
	UF ₃	3	7.30		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 4.24

LIQUID (ρ = gm/cc, T = °C) $\rho = 4.06 - 0.00094T$

LIQUID (ρ = lbs/ft³, T = °F) $\rho = 254.5 - 0.0326T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10⁴) 2.76

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^*$ =

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 300°C (572°F) $c_p = 0.18$

LIQUID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^*$ =

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 700°C (1292°F) $c_p = 0.25$

HEAT OF FUSION (cal/gm) $H_L - H_S^* =$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

<u>°C</u>	<u>(Centipoises)</u>	<u>(Centistokes)</u>	<u>°F</u>	<u>(lb./ft-hr)</u>	<u>ft²/hr</u>
-----------	----------------------	----------------------	-----------	--------------------	--------------------------

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
70	NaF	56	22.52	104.4	530°C (986°F)
	ZrF ₄	39	62.45		
	UF ₄	5	15.03		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 4.10

LIQUID (ρ = gm/cc, T = °C) $\rho = 3.90 - 0.00092T$

LIQUID (ρ = lbs/ft³, T = °F) $\rho = 244.5 - 0.0319T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10⁴) 2.83

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID (137° - 503°C)

$$H_T - H_0^{\circ C} = 1.3 + 0.1596T + 5.15 \times 10^{-5}T^2$$
$$c_p^* = 0.1596 + 10.29 \times 10^{-5}T \text{ (Ref. 4)}$$

Heat Capacity at 300°C (572°F) $c_p^* = 0.190$

LIQUID (567° - 892°C)

$$H_T - H_0^{\circ C} = 6.2 + 0.3033T - 3.24 \times 10^{-5}T^2$$
$$c_p^* = 0.3033 - 6.47 \times 10^{-5}T$$

Heat Capacity at 700°C (1292°F) $c_p^* = 0.258$

HEAT OF FUSION (cal/gm) $H_L - H_S^* = 57$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

°C	(Centipoises)	(Centistokes)	°F	(lb./ft-hr)	ft ² /hr
600	8.1* (Ref. 30)	2.42	1100	20.3*	0.0969
700	5.2*	1.60	1300	12.3*	0.0606
800	3.6*	1.14	1500	8.2*	0.0418

Exponential Form (centipoises) $\mu = 0.104e^{3798/T^{\circ K}}$

*Denotes experimental values. Other values given are calculated or estimated.

<u>Mixture</u>	<u>Component</u>	<u>Mol %</u>	<u>Wt. %</u>	<u>Avg. M.W.</u>	<u>Liquidus Temp.</u>
71	NaF ZrF ₄	54.1 45.9	22.84 77.16	99.5	520°C (968°F)

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc)

3.91

LIQUID (ρ = gm/cc, T = °C)

$$\rho = 3.70 - 0.00089T$$

LIQUID (ρ = lbs/ft³, T = °F)

$$\rho = 232.0 - 0.0309T$$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10⁴)

2.87

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^*$ =

Heat Capacity (cal/gm °C) c_p^* =

Heat Capacity at 300°C (572°F) c_p = 0.20

LIQUID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^*$ =

Heat Capacity (cal/gm °C) c_p^* =

Heat Capacity at 700°C (1292°F) c_p = 0.28

HEAT OF FUSION (cal/gm) $H_L - H_S^*$ =

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

<u>°C</u>	<u>(Centipoises)</u>	<u>(Centistokes)</u>	<u>°F</u>	<u>(lb./ft-hr)</u>	<u>ft²/hr</u>
600	7.5		1100	18.9	
700	4.6		1300	10.9	
800	3.2		1500	7.4	

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
72	NaF	20.9	9.33	94.1	490°C (914°F)
	LiF	38.4	10.58		
	ZrF ₄	35.7	63.41		
	UF ₄	5.0	16.68		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 4.04

LIQUID (ρ = gm/cc, T = °C) $\rho = 3.83 - 0.00091T$

LIQUID (ρ = lbs/ft³, T = °F) $\rho = 240.1 - 0.0315T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10⁴) 2.84

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^*$ =

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 300°C (572°F) $c_p = 0.20$

LIQUID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^*$ =

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 700°C (1292°F) $c_p = 0.28$

HEAT OF FUSION (cal/gm) $H_L - H_S^* =$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

°C	(Centipoises)	(Centistokes)	°F	(lb./ft-hr)	ft ² /hr
500	20.0* (Ref. 31)	5.88	1100	24.8*	0.1198
600	9.9*	3.0	1300	14.3*	0.0714
700	6.0*	1.88	1500	9.8*	0.0505
800	4.25*	1.36			

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

<u>Mixture</u>	<u>Component</u>	<u>Mol %</u>	<u>Wt. %</u>	<u>Avg. M.W.</u>	<u>Liquidus Temp.</u>
73	NaF	22.0	11.21	82.4	510°C (950°F)
	LiF	40.5	12.75		
	ZrF ₄	37.5	76.04		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc)

3.74

LIQUID (ρ = gm/cc, T = °C)

$$\rho = 3.52 - 0.00086T$$

LIQUID (ρ = lbs/ft³, T = °F)

$$\rho = 220.7 - 0.0298T$$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10⁴) 2.95

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm)

$$H_T - H_0^{\circ}C^* =$$

Heat Capacity (cal/gm °C)

$$c_p^* =$$

Heat Capacity at 300°C (572°F)

$$c_p = 0.22$$

LIQUID

Enthalpy (cal/gm)

$$H_T - H_0^{\circ}C^* =$$

Heat Capacity (cal/gm °C)

$$c_p^* =$$

Heat Capacity at 700°C (1292°F)

$$c_p = 0.31$$

HEAT OF FUSION (cal/gm)

$$H_L - H_S^* =$$

Thermal Conductivity

K (BTU/hr ft °F)

VISCOSITY

<u>°C</u>	<u>(Centipoises)</u>	<u>(Centistokes)</u>	<u>°F</u>	<u>(lb./ft-hr)</u>	<u>ft²/hr</u>
500	19.0		1100	23.7	
600	9.4		1300	13.7	
700	5.7		1500	9.3	
800	4.05				

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
74	LiF	69	55.13	32.4	505°C (941°F)

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc)

2.14

LIQUID (ρ = gm/cc, T = °C)

$\rho^* = 2.16 - 0.00040T$ (Ref. 3)

LIQUID (ρ = lbs/ft³, T = °F)

$\rho^* = 135.3 - 0.0139T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION ($1/^\circ\text{C} \times 10^4$)

2.13

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm) $H_T - H_0^\circ\text{C}^* =$

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 300°C (572°F) $c_p = 0.48$

LIQUID

Enthalpy (cal/gm) $H_T - H_0^\circ\text{C}^* =$

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 700°C (1292°F) $c_p = 0.67$

HEAT OF FUSION (cal/gm)

$H_L - H_S^* =$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

°C	(Centipoises)	(Centistokes)	°F	(lb./ft-hr)	ft²/hr
600	7.5**	3.90	1100	18.9**	0.1577
700	4.9**	2.60	1300	11.6**	0.0994
800	3.45**	1.89	1500	8.0**	0.0700

Exponential Form (centipoises) $\mu = 0.118e^{3624/T^\circ\text{K}}$

*Denotes experimental values. Other values given are calculated or estimated.

**Average values, Refs. 3 and 27.

<u>Mixture</u>	<u>Component</u>	<u>Mol %</u>	<u>Wt. %</u>	<u>Avg. M.W.</u>	<u>Liquidus Temp.</u>
75	LiF	67.0	43.92	39.5	464°C (867°F)
	BeF ₂	30.5	36.24		
	UF ₄	2.5	19.84		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc)	2.48
LIQUID (ρ = gm/cc, T = °C)	$\rho = 2.38 - 0.00040T$
LIQUID (ρ = lbs/ft ³ , T = °F)	$\rho = 149.0 - 0.0139T$
MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10 ⁴)	1.90

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm)	$H_T - H_0^{\circ}C^*$ =
Heat Capacity (cal/gm °C)	$c_p^* =$
Heat Capacity at 300°C (572°F)	$c_p = 0.41$

LIQUID

Enthalpy (cal/gm)	$H_T - H_0^{\circ}C^*$ =
Heat Capacity (cal/gm °C)	$c_p^* =$
Heat Capacity at 700°C (1292°F)	$c_p = 0.57$

$$\text{HEAT OF FUSION (cal/gm)} \quad H_L - H_S^* =$$

THERMAL CONDUCTIVITY

$$K (\text{BTU/hr ft } ^\circ\text{F})$$

VISCOSITY

<u>°C</u>	<u>(Centipoises)</u>	<u>(Centistokes)</u>	<u>°F</u>	<u>(lb./ft-hr)</u>	<u>ft²/hr</u>
600	8.4		1100	21.1	
700	5.5		1300	13.1	
800	3.85		1500	9.0	

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
76	NaF	55.5	45.80	50.9	400°C (752°F)
	BeF ₂	42.0	38.78		
	UF ₄	2.5	15.42		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 2.61

LIQUID (ρ = gm/cc, T = °C) $\rho = 2.50 - 0.00043T$

LIQUID (ρ = lbs/ft³, T = °F) $\rho = 156.5 - 0.0149T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10⁴) 1.95

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^*$ =

Heat Capacity (cal/gm °C) c_p^* =

Heat Capacity at 300°C (572°F) $c_p = 0.33$

LIQUID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^*$ =

Heat Capacity (cal/gm °C) c_p^* =

Heat Capacity at 700°C (1292°F) $c_p = 0.46$

HEAT OF FUSION (cal/gm) $H_L - H_S^* =$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

°C	(Centipoises)	(Centistokes)	°F	(lb./ft-hr)	ft ² /hr
600	10.5		1100	26.6	
700	6.0		1300	14.2	
800	3.75		1500	8.6	

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

<u>Mixture</u>	<u>Component</u>	<u>Mol %</u>	<u>Wt. %</u>	<u>Avg. M.W.</u>	<u>Liquidus Temp.</u>
77	NaF BeF ₂	70 30	67.59 32.41	43.5	590°C (1094°F)

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc)	2.46
LIQUID (ρ = gm/cc, T = °C)	$\rho^* = 2.41 - 0.00050T$ (Ref. 3)
LIQUID (ρ = lbs/ft ³ , T = °F)	$\rho^* = 151.0 - 0.0173T$
MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10 ⁴)	2.43

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm)	$H_T - H_0$ °C * =
Heat Capacity (cal/gm °C)	$c_p^* =$
Heat Capacity at 300°C (572°F)	$c_p = 0.36$

LIQUID

Enthalpy (cal/gm)	$H_T - H_0$ °C * =
Heat Capacity (cal/gm °C)	$c_p^* =$
Heat Capacity at 700°C (1292°F)	$c_p = 0.50$

<u>HEAT OF FUSION (cal/gm)</u>	$H_L - H_S^* =$
--------------------------------	-----------------

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

<u>°C</u>	<u>(Centipoises)</u>	<u>(Centistokes)</u>	<u>°F</u>	<u>(lb./ft-hr)</u>	<u>ft²/hr</u>
600	5.0* (Ref. 3)	2.37	1100	12.5*	0.0944
700	3.9*	1.77	1300	8.6*	0.0669
800	2.8*	1.39	1500	6.5*	0.0519

$$\text{Exponential Form (centipoises)} \quad \mu = 0.223 e^{2716/T^\circ K}$$

*Denotes experimental values. Other values given are calculated or estimated.

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
78	NaF	56	57.60	40.8	478°C (892°F)
	LiF	16	10.17		
	BeF ₂	28	32.23		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 2.42

LIQUID (ρ = gm/cc, T = °C) $\rho^* = 2.22 - 0.00041T$ (Ref. 3)

LIQUID (ρ = lbs/ft³, T = °F) $\rho^* = 139.0 - 0.0142T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10⁴) 2.11

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm) $H_T - H_0^{\circ C} =$

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 300°C (572°F) $c_p = 0.38$

LIQUID

Enthalpy (cal/gm) $H_T - H_0^{\circ C} =$

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 700°C (1292°F) $c_p = 0.53$

HEAT OF FUSION (cal/gm) $H_L - H_S^* =$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

°C	(Centipoises)	(Centistokes)	°F	(lb./ft-hr)	ft ² /hr
600	6.0**	3.03	1100	15.0**	0.1213
700	4.0**	2.07	1300	9.5**	0.0788
800	2.85**	1.50	1500	6.6**	0.0559

Exponential Form (centipoises) $\mu = 0.111e^{3486/T^{\circ K}}$

*Denotes experimental values. Other values given are calculated or estimated.

**Average values, Refs. 3 and 32.

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
79	NaF	55.0	48.36	47.8	470°C (878°F)
	LiF	15.0	8.14		
	BeF ₂	27.5	27.07		
	UF ₄	2.5	16.43		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 2.70

LIQUID ($\rho = \text{gm/cc}$, $T = ^\circ\text{C}$) $\rho = 2.60 - 0.00045T$

LIQUID ($\rho = \text{lbs}/\text{ft}^3$, $T = ^\circ\text{F}$) $\rho = 162.8 - 0.0156T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION ($1/\text{ }^\circ\text{C} \times 10^4$) 1.98

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm) $H_T - H_0^\circ\text{C}^* =$

Heat Capacity (cal/gm $^\circ\text{C}$) $c_p^* =$

Heat Capacity at 300°C (572°F) $c_p = 0.33$

LIQUID

Enthalpy (cal/gm) $H_T - H_0^\circ\text{C}^* =$

Heat Capacity (cal/gm $^\circ\text{C}$) $c_p^* =$

Heat Capacity at 700°C (1292°F) $c_p = 0.47$

HEAT OF FUSION (cal/gm) $H_L - H_S^* =$

THERMAL CONDUCTIVITY

K (BTU/hr ft $^\circ\text{F}$)

VISCOSITY

$^\circ\text{C}$	(Centipoises)	(Centistokes)	$^\circ\text{F}$	(lb./ft-hr)	ft^2/hr
600	6.6		1100	16.7	
700	4.4		1300	10.5	
800	3.15		1500	7.3	

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
80	NaF	51	43.12	49.7	605°C (1121°F)
	LiF	38	19.85		
	ZrF ₄	11	37.02		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 3.08

LIQUID (ρ = gm/cc, T = °C) $\rho = 2.95 - 0.00077T$

LIQUID (ρ = lbs/ft³, T = °F) $\rho = 185.0 - 0.0267T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10⁴) 3.21

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^*$ =

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 300°C (572°F) $c_p = 0.27$

LIQUID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^*$ =

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 700°C (1292°F) $c_p = 0.38$

HEAT OF FUSION (cal/gm) $H_L - H_S^* =$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

°C	(Centipoises)	(Centistokes)	°F	(lb./ft-hr)	ft ² /hr
----	---------------	---------------	----	-------------	---------------------

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

<u>Mixture</u>	<u>Component</u>	<u>Mol %</u>	<u>Wt. %</u>	<u>Avg. M.W.</u>	<u>Liquidus Temp.</u>
81	NaF	22	14.91	62.0	570°C (1058°F)
	LiF	55	23.03		
	ZrF ₄	23	62.06		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 3.41

LIQUID (ρ = gm/cc, T = °C) $\rho = 3.22 - 0.00081T$

LIQUID (ρ = lbs/ft³, T = °F) $\rho = 201.9 - 0.0281T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10⁴) 3.06

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID (106°-368°C)

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^* = -1.5 + 0.2392T + 7.20 \times 10^{-5}T^2$

Heat Capacity (cal/gm °C) $c_p^* = 0.2392 + 14.39 \times 10^{-5}T$ (Ref. 33)

Heat Capacity at 300°C (572°F) $c_p^* = 0.282$

LIQUID (603°-897°C)

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^* = -13.0 + 0.4526T - 5.95 \times 10^{-5}T^2$

Heat Capacity (cal/gm °C) $c_p^* = 0.4526 - 11.89 \times 10^{-5}T$

Heat Capacity at 700°C (1292°F) $c_p^* = 0.369$

HEAT OF FUSION (cal/gm) $H_L - H_S^* =$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

°C	(Centipoises)	(Centistokes)	°F	(lb./ft-hr)	ft ² /hr
600	12.0* (Ref. 34)	4.4	1100	30.3*	0.1771
700	7.0*	2.64	1300	16.5*	0.0997
800	4.45*	1.73	1500	10.2*	0.0638
900	3.05*	1.22			

Exponential Form (centipoises) $\mu = 0.0585e^{4647/T^{\circ}K}$

*Denotes experimental values. Other values given are calculated or estimated.

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
82	NaF	20	11.93	70.3	545°C (1013°F)
	LiF	55	20.30		
	ZrF ₄	21	49.92		
	UF ₄	4	17.85		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 3.70

LIQUID (ρ = gm/cc, T = °C) $\rho = 3.49 - 0.00085T$

LIQUID (ρ = lbs/ft³, T = °F) $\rho = 218.8 - 0.0295T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10⁴) 2.93

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID (98° - 363°C)

$$\text{Enthalpy (cal/gm)} \quad H_T - H_0^{\circ\text{C}} * = -3.7 + 0.2304T + 4.07 \times 10^{-5}T^2$$
$$\text{Heat Capacity (cal/gm }^{\circ}\text{C}) \quad c_p^* = 0.2304 + 8.14 \times 10^{-5}T \text{ (Ref. 4)}$$
$$\text{Heat Capacity at } 300^{\circ}\text{C (572°F)} \quad c_p^* = 0.255$$

LIQUID (582°-900°C)

$$\text{Enthalpy (cal/gm)} \quad H_T - H_0^{\circ\text{C}} * = -20.1 + 0.4314T - 7.42 \times 10^{-5}T^2$$
$$\text{Heat Capacity (cal/gm }^{\circ}\text{C}) \quad c_p^* = 0.4314 - 14.85 \times 10^{-5}T$$
$$\text{Heat Capacity at } 700^{\circ}\text{C (1292°F)} \quad c_p^* = 0.327$$

HEAT OF FUSION (cal/gm) $H_L - H_S^* =$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

°C	(Centipoises)	(Centistokes)	°F	(lb./ft-hr)	ft ² /hr
600	12.0* (Ref. 34)	4.03	1100	30.3*	0.1626
700	7.0*	2.42	1300	16.5*	0.0915
800	4.45*	1.61	1500	10.2*	0.0586

$$\text{Exponential Form (centipoises)} \quad \mu = 0.0585e^{4647/T^K}$$

*Denotes experimental values. Other values given are calculated or estimated.

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
83	NaF ZrF ₄	81 19	51.71 48.29	65.8	750°C (1382°F)

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 3.40

LIQUID (ρ = gm/cc, T = °C) $\rho = 3.22 - 0.00081T$

LIQUID (ρ = lbs/ft³, T = °F) $\rho = 201.9 - 0.0281T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10⁴) 3.06

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^*$ =

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 300°C (572°F) $c_p = 0.23$

LIQUID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^*$ =

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 700°C (1292°F) $c_p =$

HEAT OF FUSION (cal/gm) $H_L - H_S^* =$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

°C	(Centipoises)	(Centistokes)	°F	(lb./ft-hr)	ft ² /hr
----	---------------	---------------	----	-------------	---------------------

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
84	NaF	27	29.62	38.3	338°C (640°F)
	LiF	35	23.72		
	BeF ₂	38	46.66		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 2.25

LIQUID (ρ = gm/cc, T = °C) $\rho^* = 2.22 - 0.00041T$ (Ref. 35)

LIQUID (ρ = lbs/ft³, T = °F) $\rho^* = 139.0 - 0.0142T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10⁴) 2.09

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm) $H_T - H_0$ °C * =

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 300°C (572°F) $c_p = 0.42$

LIQUID

Enthalpy (cal/gm) $H_T - H_0$ °C * =

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 700°C (1292°F) $c_p = 0.59$

HEAT OF FUSION (cal/gm) $H_L - H_S^* =$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

°C	(Centipoises)	(Centistokes)	°F	(lb./ft-hr)	ft ² /hr
600	7.8* (Ref. 35)	3.91	1100	19.8*	0.1586
700	4.45*	2.27	1300	10.5*	0.0858
800	2.8*	1.48	1500	6.3*	0.0530

Exponential Form (centipoises) $\mu = 0.0338e^{4738/T^{\circ}K}$

*Denotes experimental values. Other values given are calculated or estimated.

<u>Mixture</u>	<u>Component</u>	<u>Mol %</u>	<u>Wt. %</u>	<u>Avg. M.W.</u>	<u>Liquidus Temp.</u>
85	NaF	26.5	24.62	45.2	360°C (680°F)
	LiF	34.0	19.52		
	BeF ₂	37.0	38.50		
	UF ₄	2.5	17.36		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 2.54

LIQUID ($\rho = \text{gm/cc}$, $T = {}^\circ\text{C}$) $\rho^* = 2.33 - 0.00018T$ (Ref. 35)

LIQUID ($\rho = \text{lbs}/\text{ft}^3$, $T = {}^\circ\text{F}$) $\rho^* = 145.7 - 0.00624T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION ($1/{}^\circ\text{C} \times 10^4$)

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm) $H_T - H_0 {}^\circ\text{C}^*$ =

Heat Capacity (cal/gm ${}^\circ\text{C}$) $c_p^* =$

Heat Capacity at 300°C (572°F) $c_p = 0.37$

LIQUID

Enthalpy (cal/gm) $H_T - H_0 {}^\circ\text{C}^*$ =

Heat Capacity (cal/gm ${}^\circ\text{C}$) $c_p^* =$

Heat Capacity at 700°C (1292°F) $c_p = 0.51$

HEAT OF FUSION (cal/gm) $H_L - H_S^* =$

THERMAL CONDUCTIVITY

K (BTU/hr ft ${}^\circ\text{F}$)

VISCOSITY

<u>°C</u>	<u>(Centipoises)</u>	<u>(Centistokes)</u>	<u>°F</u>	<u>(lb./ft-hr)</u>	<u>ft²/hr</u>
600	9.0* (Ref. 35)	4.04	1100	22.7*	0.1631
700	4.95*	2.24	1300	11.7*	0.0848
800	3.05*	1.41	1500	6.9*	0.0506

Exponential Form (centipoises) $\mu = 0.0261e^{5094/T^\circ\text{K}}$

*Denotes experimental values. Other values given are calculated or estimated.

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
86	LiF	35	10.87	83.6	445°C (833°F)
	NaF	32	16.08		
	ZrF ₄	29	58.02		
	UF ₄	4	15.03		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 3.87

LIQUID (ρ = gm/cc, T = °C) $\rho = 3.66 - 0.00088T$

LIQUID (ρ = lbs/ft³, T = °F) $\rho = 229.4 - 0.0305T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10⁴) 2.89

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^*$ =

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 300°C (572°F) $c_p = 0.21$

LIQUID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^*$ =

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 700°C (1292°F) $c_p = 0.29$

HEAT OF FUSION (cal/gm) $H_L - H_S^* =$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

°C	(Centipoises)	(Centistokes)	°F	(lb./ft-hr)	ft ² /hr
500	20.5* (Ref. 36)	6.37	1100	26.6*	0.1357
600	10.5*	3.35	1300	15.4*	0.0811
700	6.45*	2.12	1500	10.5*	0.0572
800	4.55*	1.54			

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
87	RbF	48	35.08	143.0	425°C (797°F)
	ZrF ₄	48	56.13		
	UF ₄	4	8.79		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 4.19

LIQUID (ρ = gm/cc, T = °C) $\rho = 4.00 - 0.00093T$

LIQUID (ρ = lbs/ft³, T = °F) $\rho = 250.7 - 0.0322T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10⁴) 2.78

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID (142°-398°C)

$$H_T - H_0^{\circ C} * = -3.2 + 0.1490T + 3.2 \times 10^{-5} T^2$$

$$c_p^* = 0.1490 + 6.5 \times 10^{-5} T \text{ (Ref. 37)}$$

$$c_p^* = 0.169$$

LIQUID (458°-880°C)

$$H_T - H_0^{\circ C} * = -9.8 + 0.2844T - 5.4 \times 10^{-5} T^2$$

$$c_p^* = 0.2844 - 10.8 \times 10^{-5} T$$

$$c_p^* = 0.209$$

HEAT OF FUSION (cal/gm)

$$H_L - H_S^* = 35$$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F) 1.0 (Liquid, constant gap) (Ref. 45)

VISCOSITY

°C	(Centipoises)	(Centistokes)	°F	(lb./ft-hr)	ft ² /hr
600	7.1* (Ref. 38)	2.11	1100	17.8*	0.0844
700	4.65*	1.41	1300	11.0*	0.0537
800	3.3*	1.03	1500	7.6*	0.0382

Exponential Form (centipoises) $\mu = 0.116e^{3590/T^{\circ K}}$

PRANDTL NUMBER 3.9 at 1100°F, 2.3 at 1300°F, 1.5 at 1500°F

*Denotes experimental values. Other values given are calculated or estimated.

<u>Mixture</u>	<u>Component</u>	<u>Mol %</u>	<u>Wt. %</u>	<u>Avg. M.W.</u>	<u>Liquidus Temp.</u>
88	NaF	64	62.88	42.8	555°C (1031°F)
	LiF	5	3.04		
	BeF ₂	31	34.08		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc)	2.44
LIQUID (ρ = gm/cc, T = °C)	$\rho^* = 2.39 - 0.00050T$ (Ref. 3)
LIQUID (ρ = lbs/ft ³ , T = °F)	$\rho^* = 149.7 - 0.0173T$
MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10 ⁴)	2.45

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm)	$H_T - H_0°C^*$ =
Heat Capacity (cal/gm °C)	$c_p^* =$
Heat Capacity at 300°C (572°F)	$c_p = 0.37$

LIQUID

Enthalpy (cal/gm)	$H_T - H_0°C^*$ =
Heat Capacity (cal/gm °C)	$c_p^* =$
Heat Capacity at 700°C (1292°F)	$c_p = 0.51$

<u>HEAT OF FUSION (cal/gm)</u>	$H_L - H_S^* =$
--------------------------------	-----------------

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

<u>°C</u>	<u>(Centipoises)</u>	<u>(Centistokes)</u>	<u>°F</u>	<u>(lb./ft-hr)</u>	<u>ft²/hr</u>
600	7.1**	3.39	1100	17.8**	0.1364
700	4.75**	2.32	1300	11.3**	0.0887
800	3.4*	1.71	1500	7.9**	0.0636

$$\text{Exponential Form (centipoises)} \quad \mu = 0.138e^{3435/T^K}$$

*Denotes experimental values. Other values given are calculated or estimated.
**Average values, Refs. 3 and 39.

<u>Mixture</u>	<u>Component</u>	<u>Mol %</u>	<u>Wt. %</u>	<u>Avg. M.W.</u>	<u>Liquidus Temp.</u>
89	NaF	63.5	63.12	42.2	535°C (995°F)
	LiF	7.5	4.62		
	BeF ₂	29.0	32.26		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 2.44

LIQUID (ρ = gm/cc, T = °C) $\rho^* = 2.38 - 0.00051T$ (Ref. 3)

LIQUID (ρ = lbs/ft³, T = °F) $\rho^* = 149.1 - 0.0177T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10⁴) 2.52

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^*$ =

Heat Capacity (cal/gm °C) c_p^* =

Heat Capacity at 300°C (572°F) $c_p = 0.37$

LIQUID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^*$ =

Heat Capacity (cal/gm °C) c_p^* =

Heat Capacity at 700°C (1292°F) $c_p = 0.51$

HEAT OF FUSION (cal/gm) $H_L - H_S^* =$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

<u>°C</u>	<u>(Centipoises)</u>	<u>(Centistokes)</u>	<u>°F</u>	<u>(lb./ft-hr)</u>	<u>ft²/hr</u>
600	7.0* (Ref. 3)	3.37	1100	17.4*	0.1340
700	4.6*	2.28	1300	10.9*	0.0864
800	3.3*	1.67	1500	7.6*	0.0620

Exponential Form (centipoises) $\mu = 0.121e^{3543/T^{\circ}K}$

*Denotes experimental values. Other values given are calculated or estimated.

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
90	NaF	49	45.00	46.2	555°C (1031°F)
	KF	15	17.95		
	BeF ₂	36	37.05		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 2.38

LIQUID (ρ = gm/cc, T = °C) $\rho = 2.30 - 0.00038T$

LIQUID (ρ = lbs/ft³, T = °F) $\rho = 144.0 - 0.0132T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10⁴) 1.86

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^*$ =

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 300°C (572°F) $c_p = 0.35$

LIQUID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^*$ =

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 700°C (1292°F) $c_p = 0.48$

HEAT OF FUSION (cal/gm) $H_L - H_S^* =$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

°C	(Centipoises)	(Centistokes)	°F	(lb./ft-hr)	ft ² /hr
600	8.0* (Ref. 40)	3.86	1100	20.1*	0.1555
700	5.0*	2.46	1300	11.9*	0.0937
800	3.4*	1.70	1500	7.9*	0.0634

Exponential Form (centipoises) $\mu = 0.0811e^{4008/T^{\circ}K}$

*Denotes experimental values. Other values given are calculated or estimated.

<u>Mixture</u>	<u>Component</u>	<u>Mol %</u>	<u>Wt. %</u>	<u>Avg. M.W.</u>	<u>Liquidus Temp.</u>
91	NaF	53	38.86	57.3	590°C (1094°F)
	LiF	35	15.85		
	ZrF ₄	8	23.36		
	UF ₄	4	21.93		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 3.40

LIQUID (ρ = gm/cc, T = °C) $\rho = 3.22 - 0.00081T$

LIQUID (ρ = lbs/ft³, T = °F) $\rho = 201.9 - 0.0281T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10⁴) 3.06

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^*$ =

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 300°C (572°F) $c_p = 0.24$

LIQUID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^*$ =

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 700°C (1292°F) $c_p = 0.33$

HEAT OF FUSION (cal/gm) $H_L - H_S^* =$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

<u>°C</u>	<u>(Centipoises)</u>	<u>(Centistokes)</u>	<u>°F</u>	<u>(lb./ft-hr)</u>	<u>ft²/hr</u>
600	10.5		1100	26.6	
700	6.45		1300	15.4	
800	4.55		1500	10.5	

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
92	NaF	49.5	40.61	51.2	415°C (779°F)
	BeF ₂	48.0	44.06		
	UF ₄	2.5	15.33		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc)	2.56
LIQUID (ρ = gm/cc, T = °C)	$\rho = 2.46 - 0.00042T$
LIQUID (ρ = lbs/ft ³ , T = °F)	$\rho = 154.0 - 0.0146T$
MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10 ⁴)	1.94

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm)	$H_T - H_0^{\circ}C^*$ =
Heat Capacity (cal/gm °C)	$c_p^* =$
Heat Capacity at 300°C (572°F)	$c_p = 0.34$

LIQUID

Enthalpy (cal/gm)	$H_T - H_0^{\circ}C^*$ =
Heat Capacity (cal/gm °C)	$c_p^* =$
Heat Capacity at 700°C (1292°F)	$c_p = 0.47$

<u>HEAT OF FUSION (cal/gm)</u>	$H_L - H_S^* =$
--------------------------------	-----------------

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

°C	(Centipoises)	(Centistokes)	°F	(lb./ft-hr)	ft ² /hr
600	13.7		1100	34.6	
700	7.3		1300	17.3	
800	4.4		1500	9.9	

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
93	LiF	50	12.66	102.4	550°C (1022°F)
	ZrF ₄	46	75.08		
	UF ₄	4	12.26		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 4.12

LIQUID (ρ = gm/cc, T = °C) $\rho = 3.92 - 0.00092T$

LIQUID (ρ = lbs/ft³, T = °F) $\rho = 245.7 - 0.0319T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10⁴) 2.81

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^*$ =

Heat Capacity (cal/gm °C) c_p^* =

Heat Capacity at 300°C (572°F) $c_p = 0.20$

LIQUID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^*$ =

Heat Capacity (cal/gm °C) c_p^* =

Heat Capacity at 700°C (1292°F) $c_p = 0.28$

HEAT OF FUSION (cal/gm) $H_L - H_S^*$ =

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

<u>°C</u>	<u>(Centipoises)</u>	<u>(Centistokes)</u>	<u>°F</u>	<u>(lb./ft-hr)</u>	<u>ft²/hr</u>
-----------	----------------------	----------------------	-----------	--------------------	--------------------------

Exponential Form (centipoises)

<u>Mixture</u>	<u>Component</u>	<u>Mol %</u>	<u>Wt. %</u>	<u>Avg. M.W.</u>	<u>Liquidus Temp.</u>
94	KF	50	24.51	118.5	
	ZrF ₄	46	64.89		
	UF ₄	4	10.60		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 3.83

LIQUID (ρ = gm/cc, T = °C) $\rho = 3.61 - 0.00087T$

LIQUID (ρ = lbs/ft³, T = °F) $\rho = 226.3 - 0.0302T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10⁴) 2.90

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm) $H_T - H_0^{\circ C} * =$

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 300°C (572°F) $c_p = 0.17$

LIQUID

Enthalpy (cal/gm) $H_T - H_0^{\circ C} * =$

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 700°C (1292°F) $c_p = 0.24$

HEAT OF FUSION (cal/gm) $H_L - H_S^* =$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

<u>°C</u>	<u>(Centipoises)</u>	<u>(Centistokes)</u>	<u>°F</u>	<u>(lb./ft-hr)</u>	<u>ft²/hr</u>
-----------	----------------------	----------------------	-----------	--------------------	--------------------------

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
95	RbF	50	36.87	141.7	500°C (932°F)
	ZrF ₄	46	54.27		
	UF ₄	4	8.86		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 4.18

LIQUID (ρ = gm/cc, T = °C) $\rho = 4.00 - 0.00093T$

LIQUID (ρ = lbs/ft³, T = °F) $\rho = 250.7 - 0.0322T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10⁴) 2.78

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^*$ =

Heat Capacity (cal/gm °C) c_p^* =

Heat Capacity at 300°C (572°F) $c_p = 0.14$

LIQUID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^*$ =

Heat Capacity (cal/gm °C) c_p^* =

Heat Capacity at 700°C (1292°F) $c_p = 0.20$

HEAT OF FUSION (cal/gm) $H_L - H_S^* =$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

°C	(Centipoises)	(Centistokes)	°F	(lb./ft-hr)	ft ² /hr
600	7.05* (Ref. 38)	2.06	1100	17.9*	0.0837
700	4.35*	1.31	1300	10.4*	0.0501
800	2.95*	0.91	1500	6.8*	0.0338

Exponential Form (centipoises) $\mu = 0.0657e^{4081/T^{\circ}K}$

*Denotes experimental values. Other values given are calculated or estimated.

<u>Mixture</u>	<u>Component</u>	<u>Mol %</u>	<u>Wt. %</u>	<u>Avg. M.W.</u>	<u>Liquidus Temp.</u>
96	NaF	53	56.66	39.3	535°C (995°F)
	LiF	24	15.83		
	BeF ₂	23	27.51		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 2.43
LIQUID (ρ = gm/cc, T = °C) $\rho = 2.34 - 0.00039T$
LIQUID (ρ = lbs/ft³, T = °F) $\rho = 146.5 - 0.0135T$
MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10⁴) 1.88

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^*$ =
Heat Capacity (cal/gm °C) $c_p^* =$
Heat Capacity at 300°C (572°F) $c_p = 0.38$

LIQUID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^*$ =
Heat Capacity (cal/gm °C) $c_p^* =$
Heat Capacity at 700°C (1292°F) $c_p = 0.54$

HEAT OF FUSION (cal/gm) $H_L - H_S^* =$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

<u>°C</u>	<u>(Centipoises)</u>	<u>(Centistokes)</u>	<u>°F</u>	<u>(lb./ft-hr)</u>	<u>ft²/hr</u>
600	5.9* (Ref. 40)	2.80	1100	14.8*	0.1121
700	4.1*	1.98	1300	9.7*	0.0749
800	3.0*	1.47	1500	6.9*	0.0543

Exponential Form (centipoises) $\mu = 0.157e^{3168/T^{\circ}K}$

*Denotes experimental values. Other values given are calculated or estimated.

<u>Mixture</u>	<u>Component</u>	<u>Mol %</u>	<u>Wt. %</u>	<u>Avg. M.W.</u>	<u>Liquidus Temp.</u>
97	NaF	49	55.70	37.0	597°C (1107°F)
	LiF	36	25.22		
	BeF ₂	15	19.08		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 2.47

LIQUID (ρ = gm/cc, T = °C) $\rho = 2.37 - 0.00039T$

LIQUID (ρ = lbs/ft³, T = °F) $\rho = 148.4 - 0.0135T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10⁴) 1.87

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^* =$

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 300°C (572°F) $c_p = 0.39$

LIQUID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^* =$

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 700°C (1292°F) $c_p = 0.55$

HEAT OF FUSION (cal/gm) $H_L - H_S^* =$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

<u>°C</u>	<u>(Centipoises)</u>	<u>(Centistokes)</u>	<u>°F</u>	<u>(lb./ft-hr)</u>	<u>ft²/hr</u>
600	5.65* (Ref. 41)	2.65	1100	14.0*	0.1053
700	3.95*	1.89	1300	9.4*	0.0720
800	2.95*	1.44	1500	6.9*	0.0540

Exponential Form (centipoises) $\mu = 0.173e^{3043/T^{\circ}K}$

*Denotes experimental values. Other values given are calculated or estimated.

<u>Mixture</u>	<u>Component</u>	<u>Mol %</u>	<u>Wt. %</u>	<u>Avg. M.W.</u>	<u>Liquidus Temp.</u>
98	NaF	56	49.23	47.8	505°C (941°F)
	LiF	21	11.39		
	BeF ₂	20	19.67		
	UF ₄	3	19.72		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 2.82

LIQUID (ρ = gm/cc, T = °C) $\rho = 2.72 - 0.00048T$

LIQUID (ρ = lbs/ft³, T = °F) $\rho = 170.3 - 0.0166T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10⁴) 2.03

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^* =$

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 300°C (572°F) $c_p = 0.32$

LIQUID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^* =$

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 700°C (1292°F) $c_p = 0.45$

HEAT OF FUSION (cal/gm) $H_L - H_S^* =$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

<u>°C</u>	<u>(Centipoises)</u>	<u>(Centistokes)</u>	<u>°F</u>	<u>(lb./ft-hr)</u>	<u>ft²/hr</u>
600	7.3* (Ref. 41)	3.0	1100	18.4*	0.1215
700	4.6*	1.94	1300	10.9*	0.0737
800	3.1*	1.34	1500	7.1*	0.0492

Exponential Form (centipoises) $\mu = 0.0737e^{4012/T^{\circ}K}$

*Denotes experimental values. Other values given are calculated or estimated.

<u>Mixture</u>	<u>Component</u>	<u>Mol %</u>	<u>Wt. %</u>	<u>Avg. M.W.</u>	<u>Liquidus Temp.</u>
99	NaF	63.5	23.22	114.9	607°C (1125°F)
	ZrF ₄	18.0	26.20		
	UF ₄	18.5	50.58		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 4.59

LIQUID (ρ = gm/cc, T = °C) $\rho = 4.46 - 0.0010T$

LIQUID (ρ = lbs/ft³, T = °F) $\rho = 279.5 - 0.0347T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10⁴) 2.66

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm) $H_T - H_0^{\circ C} * =$

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 300°C (572°F) $c_p = 0.16$

LIQUID

Enthalpy (cal/gm) $H_T - H_0^{\circ C} * =$

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 700°C (1292°F) $c_p = 0.22$

HEAT OF FUSION (cal/gm) $H_L - H_S^* =$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

°C (Centipoises) (Centistokes) °F (lb./ft-hr) ft²/hr

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
100	LiF	60	48.08	32.3	652°C (1206°F)
	NaF	40	51.92		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc)	2.53
LIQUID (ρ = gm/cc, T = °C)	$\rho^* = 2.42 - 0.00055T$ (Ref. 16)
LIQUID (ρ = lbs/ft³, T = °F)	$\rho^* = 151.7 - 0.0191T$
MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10⁴)	2.71

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID (112°-572°C)

Enthalpy (cal/gm)	$H_T - H_0^{\circ C} = -0.1 + 0.3191T + 9.94 \times 10^{-5}T^2$
Heat Capacity (cal/gm °C)	$c_p^* = 0.3191 + 19.87 \times 10^{-5}T$ (Ref. 42)
Heat Capacity at 300°C (572°F)	$c_p^* = 0.379$

LIQUID (688°-898°C)

Enthalpy (cal/gm)	$H_T - H_0^{\circ C} = -78.5 + 0.9249T - 24.62 \times 10^{-5}T^2$
Heat Capacity (cal/gm °C)	$c_p^* = 0.9249 - 49.23 \times 10^{-5}T$
Heat Capacity at 700°C (1292°F)	$c_p^* = 0.580$

<u>HEAT OF FUSION (cal/gm)</u>	$H_L - H_S^* = 170$
--------------------------------	---------------------

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

°C	(Centipoises)	(Centistokes)	°F	(lb./ft-hr)	ft²/hr
700	3.2* (Ref. 25)	1.58	1300	7.6*	0.0597
800	2.35*	1.19	1500	5.4*	0.0439

$$\text{Exponential Form (centipoises)} \quad \mu = 0.116e^{3225/T^{\circ K}}$$

*Denotes experimental values. Other values given are calculated or estimated.

<u>Mixture</u>	<u>Component</u>	<u>Mol %</u>	<u>Wt. %</u>	<u>Avg. M.W.</u>	<u>Liquidus Temp.</u>
101	LiF	57.6	34.24	43.6	645°C (1193°F)
	NaF	38.4	36.97		
	UF ₄	4.0	28.79		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 3.08

LIQUID (ρ = gm/cc, T = °C) $\rho = 2.95 - 0.00077T$

LIQUID (ρ = lbs/ft³, T = °F) $\rho = 185.0 - 0.0267T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10⁴) 3.21

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID (97°-594°C)

$$\begin{aligned} \text{Enthalpy (cal/gm)} & H_T - H_0^{\circ C} * = 0 + 0.227T + 17 \times 10^{-5} T^2 \\ \text{Heat Capacity (cal/gm °C)} & c_p^* = 0.227 + 33 \times 10^{-5} T \text{ (Ref. 4)} \\ \text{Heat Capacity at } 300^\circ\text{C (572°F)} & c_p^* = 0.326 \end{aligned}$$

LIQUID (655°-916°C)

$$\begin{aligned} \text{Enthalpy (cal/gm)} & H_T - H_0^{\circ C} * = -68.9 + 0.531T \\ \text{Heat Capacity (cal/gm °C)} & c_p^* = 0.53 \\ \text{Heat Capacity at } 700^\circ\text{C (1292°F)} & c_p^* = 0.53 \end{aligned}$$

HEAT OF FUSION (cal/gm) $H_L - H_S^* = 56$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

<u>°C</u>	<u>(Centipoises)</u>	<u>(Centistokes)</u>	<u>°F</u>	<u>(lb./ft-hr)</u>	<u>ft²/hr</u>
700	3.5		1300	8.4	
800	2.6		1500	6.0	

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
102	LiF	50	30.85	42.1	492°C (918°F)

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc)	2.43
LIQUID (ρ = gm/cc, T = °C)	$\rho = 2.46 - 0.00068T$
LIQUID (ρ = lbs/ft³, T = °F)	$\rho = 154.3 - 0.0236T$
MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION ($1/°C \times 10^4$)	3.40

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID (107°-466°C)

Enthalpy (cal/gm)	$H_T - H_0°C^* = -2.3 + 0.2817T + 3.82 \times 10^{-5}T^2$
Heat Capacity (cal/gm °C)	$c_p^* = 0.2817 + 7.64 \times 10^{-5}T$ (Ref. 4)
Heat Capacity at 300°C (572°F)	$c_p^* = 0.305$

LIQUID (532°-893°C)

Enthalpy (cal/gm)	$H_T - H_0°C^* = -23.8 + 0.5839T - 10.28 \times 10^{-5}T^2$
Heat Capacity (cal/gm °C)	$c_p^* = 0.5839 - 20.56 \times 10^{-5}T$
Heat Capacity at 700°C (1292°F)	$c_p^* = 0.440$

HEAT OF FUSION (cal/gm)

$$H_L - H_S^* = 93$$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

°C	(Centipoises)	(Centistokes)	°F	(lb./ft-hr)	ft²/hr
600	4.75		1100	12.1	
700	2.9		1300	6.9	
800	1.95		1500	4.4	

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

<u>Mixture</u>	<u>Component</u>	<u>Mol %</u>	<u>Wt. %</u>	<u>Avg. M.W.</u>	<u>Liquidus Temp.</u>
103	LiF	48	23.55	52.9	560°C (1040°F)
	KF	48	52.70		
	UF ₄	4	23.75		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 2.85

LIQUID ($\rho = \text{gm/cc}$, $T = ^\circ\text{C}$) $\rho = 2.75 - 0.00073T$

LIQUID ($\rho = \text{lbs}/\text{ft}^3$, $T = ^\circ\text{F}$) $\rho = 172.5 - 0.0253T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION ($1/\text{ }^\circ\text{C} \times 10^4$) 3.24

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID (127°-465°C)

Enthalpy (cal/gm)

$$H_T - H_0^\circ\text{C}^* = 0.1 + 0.234T + 4.9 \times 10^{-5}T^2$$

Heat Capacity (cal/gm °C)

$$c_p^* = 0.234 + 9.7 \times 10^{-5}T \text{ (Ref. 4)}$$

Heat Capacity at 300°C (572°F)

$$c_p^* = 0.263$$

LIQUID (563°-882°C)

Enthalpy (cal/gm)

$$H_T - H_0^\circ\text{C}^* = -82.4 + 0.657T - 19.7 \times 10^{-5}T^2$$

Heat Capacity (cal/gm °C)

$$c_p^* = 0.657 - 39.3 \times 10^{-5}T$$

Heat Capacity at 700°C (1292°F)

$$c_p^* = 0.382$$

HEAT OF FUSION (cal/gm)

$$H_L - H_S^* = 68 \text{ at } 500^\circ\text{C}^{**}$$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

1.4 (solid sphere and slab)(Ref. 45)

VISCOSITY

<u>°C</u>	<u>(Centipoises)</u>	<u>(Centistokes)</u>	<u>°F</u>	<u>(lb./ft-hr)</u>	<u>ft²/hr</u>
600	5.25		1100	13.2	
700	3.2		1300	7.6	
800	2.15		1500	5.0	

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

**The major break in the enthalpy-temperature curve was at 500°C.

<u>Mixture</u>	<u>Component</u>	<u>Mol %</u>	<u>Wt. %</u>	<u>Avg. M.W.</u>	<u>Liquidus Temp.</u>
104	LiF	43	15.77	70.7	475°C (887°F)
	RbF	57	84.23		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 3.27

$$L_{T=0} = \rho^* = 3.30 - 0.00096T \quad (\text{Ref. 22})$$

$$\text{LIQUID } (\rho = \text{lbs}/\text{ft}^3, T = {}^\circ\text{F}) \quad \rho^* = 207.1 - 0.0333T$$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION ($1/{}^{\circ}\text{C} \times 10^4$) 3.65

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID (134° - 420°C)

$$\text{Enthalpy (cal/gm)} \quad H_{\text{m}} - H_{\text{O}_2}^* = -1.1 + 0.1849T + 2.45 \times 10^{-5} T^2$$

$$\text{Heat Capacity (cal/gm } ^\circ\text{C)} \quad c_p^* = 0.1849 + 4.9 \times 10^{-5} T \text{ (Ref. 37)}$$

Heat Capacity at 300°C (572°F) $\frac{c_p}{c_p^*} = 0.200$

LIQUID (497° - 878°C)

$$\text{Enthalpy (cal/gm)} \quad H_{\text{m}} - H_{\text{O}_f}^* = -22.9 + 0.3969T - 8.1 \times 10^{-5}T^2$$

$$\text{Heat Capacity (cal/gm } ^\circ\text{C)} \quad c_p^* = 0.3969 - 16.1 \times 10^{-5} T$$

Heat Capacity at 700°C (1292°F) $c_p^* = 0.284$

HEAT OF FUSION (cal/gm)

$$H_L - H_S^* = 55$$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

1.2 (Liquid) (Ref. 43)

VISCOSITY

$$\text{Exponential Form (centipoises)} \quad \mu = 0.0212e^{4678/T^\circ\text{K}}$$

PRANDTL NUMBER 2.9 at 1100° F

*Denotes experimental values. Other values given are calculated or estimated.

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
105	LiF	41.3	13.32	80.5	660°C (1220°F)
	RbF	54.7	71.06		
	UF ₄	4.0	15.62		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 3.56

LIQUID (ρ = gm/cc, T = °C) $\rho = 3.36 - 0.00084T$

LIQUID (ρ = lbs/ft³, T = °F) $\rho = 210.7 - 0.0291T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10⁴) 2.57

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^*$ =

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 300°C (572°F) $c_p = 0.18$

LIQUID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^*$ =

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 700°C (1292°F) $c_p = 0.25$

HEAT OF FUSION (cal/gm) $H_L - H_S^* =$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

<u>°C</u>	<u>(Centipoises)</u>	<u>(Centistokes)</u>	<u>°F</u>	<u>(lb./ft-hr)</u>	<u>ft²/hr</u>
-----------	----------------------	----------------------	-----------	--------------------	--------------------------

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
106	LiF	44.7	22.23	52.2	560°C (1040°F)
	KF	40.3	8.85		
	NaF	11.0	44.86		
	UF ₄	4.0	24.06		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc)	2.90
LIQUID (ρ = gm/cc, T = °C)	$\rho = 2.80 - 0.00074T$
LIQUID (ρ = lbs/ft ³ , T = °F)	$\rho = 175.6 - 0.0257T$
MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10 ⁴)	3.26

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm)	$H_T - H_0^{\circ}C^*$ =
Heat Capacity (cal/gm °C)	c_p^* =
Heat Capacity at 300°C (572°F)	c_p = 0.27

LIQUID

Enthalpy (cal/gm)	$H_T - H_0^{\circ}C^*$ =
Heat Capacity (cal/gm °C)	c_p^* =
Heat Capacity at 700°C (1292°F)	c_p = 0.38

<u>HEAT OF FUSION (cal/gm)</u>	$H_L - H_S^*$ =
--------------------------------	-----------------

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

°C	(Centipoises)	(Centistokes)	°F	(lb./ft-hr)	ft ² /hr
600	5.35		1100	13.6	
700	3.2		1300	7.6	
800	2.15		1500	4.8	

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

<u>Mixture</u>	<u>Component</u>	<u>Mol %</u>	<u>Wt. %</u>	<u>Avg. M.W.</u>	<u>Liquidus Temp.</u>
107	NaF	11.2	9.77	48.1	490°C (914°F)
	KF	41.0	49.52		
	LiF	45.3	24.39		
	UF ₄	2.5	16.32		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc)	2.74
LIQUID (ρ = gm/cc, T = °C)	$\rho = 2.67 - 0.00072T$
LIQUID (ρ = lbs/ft ³ , T = °F)	$\rho = 167.5 - 0.0250T$
MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10 ⁴)	3.32

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm)	$H_T - H_0^{\circ}C^*$ =
Heat Capacity (cal/gm °C)	$c_p^* =$
Heat Capacity at 300°C (572°F)	$c_p = 0.29$

LIQUID

Enthalpy (cal/gm)	$H_T - H_0^{\circ}C^*$ =
Heat Capacity (cal/gm °C)	$c_p^* =$
Heat Capacity at 700°C (1292°F)	$c_p = 0.41$

HEAT OF FUSION (cal/gm)

$$H_L - H_S^* =$$

THERMAL CONDUCTIVITY

$$K \text{ (BTU/hr ft } ^\circ\text{F)}$$

VISCOSITY

<u>°C</u>	<u>(Centipoises)</u>	<u>(Centistokes)</u>	<u>°F</u>	<u>(lb./ft-hr)</u>	<u>ft²/hr</u>
600	5.1* (Ref.12)	2.27	1100	12.8*	0.0909
700	3.0*	1.38	1300	7.1*	0.0523

$$\text{Exponential Form (centipoises)} \quad \mu = 0.0292e^{4507/T^\circ K}$$

*Denotes experimental values. Other values given are calculated or estimated.

<u>Mixture</u>	<u>Component</u>	<u>Mol %</u>	<u>Wt. %</u>	<u>Avg. M.W.</u>	<u>Liquidus Temp.</u>
108	NaF	56.0	22.06	106.6	550°C (1022°F)
	ZrF ₄	37.5	58.80		
	UF ₄	6.5	19.15		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 4.16

LIQUID (ρ = gm/cc, T = °C) $\rho = 3.97 - 0.00093T$

LIQUID (ρ = lbs/ft³, T = °F) $\rho = 248.9 - 0.0322T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10⁴) 2.80

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^* =$

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 300°C (572°F) $c_p = 0.18$

LIQUID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^* =$

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 700°C (1292°F) $c_p = 0.25$

HEAT OF FUSION (cal/gm) $H_L - H_S^* =$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

<u>°C</u>	<u>(Centipoises)</u>	<u>(Centistokes)</u>	<u>°F</u>	<u>(lb./ft-hr)</u>	<u>ft²/hr</u>
600	8.5		1100	21.3	
700	5.4		1300	12.8	
800	3.7		1500	8.5	

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
109	NaF	32	16.96	79.3	535°C (995°F)
	RbF	31	40.88		
	BeF ₂	31	18.38		
	UF ₄	6	23.78		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc)	3.29
LIQUID (ρ = gm/cc, T = °C)	$\rho = 3.20 - 0.00064T$
LIQUID (ρ = lbs/ft ³ , T = °F)	$\rho = 200.5 - 0.0222T$
MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10 ⁴)	2.33

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm)	$H_T - H_0^{\circ}\text{C}^*$ =
Heat Capacity (cal/gm °C)	$c_p^* =$
Heat Capacity at 300°C (572°F)	$c_p = 0.21$

LIQUID

Enthalpy (cal/gm)	$H_T - H_0^{\circ}\text{C}^*$ =
Heat Capacity (cal/gm °C)	$c_p^* =$
Heat Capacity at 700°C (1292°F)	$c_p = 0.30$

<u>HEAT OF FUSION (cal/gm)</u>	$H_L - H_S^* =$
--------------------------------	-----------------

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

$^{\circ}\text{C}$ (Centipoises) (Centistokes) $^{\circ}\text{F}$ (lb./ft-hr) ft²/hr

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
110	NaF	61.7	37.2	69.6	775°C (1427°F)
	KF	20.5	17.1		
	ZrF ₄	16.4	39.4		
	UF ₄	1.4	6.3		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 3.27* (Ref. 22)
LIQUID (ρ = gm/cc, T = °C) $\rho = 3.15 - 0.00080T$
LIQUID (ρ = lbs/ft³, T = °F) $\rho = 197.5 - 0.0277T$
MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10⁴) 3.19

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^*$ =
Heat Capacity (cal/gm °C) $c_p^* =$
Heat Capacity at 300°C (572°F) $c_p = 0.21$

LIQUID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^*$ =
Heat Capacity (cal/gm °C) $c_p^* =$
Heat Capacity at 700°C (1292°F) $c_p =$

HEAT OF FUSION (cal/gm) $H_L - H_S^* =$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

°C	(Centipoises)	(Centistokes)	°F	(lb./ft-hr)	ft ² /hr
----	---------------	---------------	----	-------------	---------------------

Exponential Form (centipoises)

*Denotes experimental values. Other values given are calculated or estimated.

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
111	LiF	71	27.86	66.02	
	BeF ₂	16	11.39		
	ThF ₄	12	56.00		
	UF ₄	1	4.76		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 3.71

LIQUID (ρ = gm/cc, T = °C) $\rho = 3.82 - 0.00082T$

LIQUID (ρ = lbs/ft³, T = °F) $\rho = 239.4 - 0.0284T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10⁴) 2.52

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^*$ =

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 300°C (572°F) $c_p = 0.26$

LIQUID

Enthalpy (cal/gm) $H_T - H_0^{\circ}C^*$ =

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 700°C (1292°F) $c_p = 0.37$

HEAT OF FUSION (cal/gm) $H_L - H_S^* =$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

°C	(Centipoises)	(Centistokes)	°F	(lb./ft-hr)	ft ² /hr
600	13.0* (Ref. 22)	3.90	1100	33.9*	0.1628
700	7.1*	2.18	1300	16.9*	0.0835
800	4.8*	1.51	1500	11.0*	0.0559

Exponential Form (centipoises) $\mu = 0.0620e^{4666/T^{\circ}K}$

*Denotes experimental values. Other values given are calculated or estimated.

<u>Mixture</u>	<u>Component</u>	<u>Mol %</u>	<u>Wt. %</u>	<u>Avg. M.W.</u>	<u>Liquidus Temp.</u>
112	LiF BeF ₂	50 50	35.53 64.47	36.5	350°C (662°F)

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc)	2.08
LIQUID (ρ = gm/cc, T = °C)	$\rho^* = 2.22 - 0.00040T$ (Ref. 3)
LIQUID (ρ = lbs/ft ³ , T = °F)	$\rho^* = 139.0 - 0.0139T$
MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10 ⁴)	2.06

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm)	$H_T - H_0$ °C * =
Heat Capacity (cal/gm °C)	$c_p^* =$
Heat Capacity at 300°C (572°F)	$c_p = 0.46$

LIQUID

Enthalpy (cal/gm)	$H_T - H_0$ °C * =
Heat Capacity (cal/gm °C)	$c_p^* =$
Heat Capacity at 700°C (1292°F)	$c_p = 0.65$

HEAT OF FUSION (cal/gm) $H_L - H_S^* =$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

°C	(Centipoises)	(Centistokes)	°F	(lb./ft-hr)	ft ² /hr
600	22.2* (Ref. 3)	11.2	1100	56.9*	0.4874
700	10.7*	5.52	1300	25.2*	0.2200
800	5.95*	3.12	1500	13.3*	0.1184

$$\text{Exponential Form (centipoises)} \quad \mu = 0.0189e^{6174/T_K}$$

*Denotes experimental values. Other values given are calculated or estimated.

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
113	NaF BeF ₂	50 50	47.19 52.81	44.5	380°C (716°F)

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 2.45* (Ref. 10)

LIQUID (ρ = gm/cc, T = °C) $\rho = 2.25 - 0.00040T$

LIQUID (ρ = lbs/ft³, T = °F) $\rho = 140.9 - 0.0139T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10⁴) 2.02

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm) $H_T - H_0^{\circ C} * =$

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 300°C (572°F) $c_p = 0.38$

LIQUID

Enthalpy (cal/gm) $H_T - H_0^{\circ C} * =$

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 700°C (1292°F) $c_p = 0.53$

HEAT OF FUSION (cal/gm) $H_L - H_S^* =$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

°C	(Centipoises)	(Centistokes)	°F	(lb./ft-hr)	ft ² /hr
600	15.3*(Ref.44)	7.61	1100	38.7*	0.3084
700	8.4*	4.26	1300	20.1*	0.1634
800	5.25*	2.72	1500	11.9*	0.0988

Exponential Form (centipoises) $\mu = 0.0493e^{5009/T^{\circ K}}$

*Denotes experimental values. Other values given are calculated or estimated.

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
114	KF	50	55.28	52.6	445°C (833°F)
	BeF ₂	50	44.72		

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 2.23

LIQUID (ρ = gm/cc, T = °C) $\rho = 2.18 - 0.00035T$

LIQUID (ρ = lbs/ft³, T = °F) $\rho = 136.5 - 0.0121T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10⁴) 1.81

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm) $H_T - H_0^{\circ}\text{C}^* =$

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 300°C (572°F) $c_p = 0.32$

LIQUID

Enthalpy (cal/gm) $H_T - H_0^{\circ}\text{C}^* =$

Heat Capacity (cal/gm °C) $c_p^* =$

Heat Capacity at 700°C (1292°F) $c_p = 0.45$

HEAT OF FUSION (cal/gm) $H_L - H_S^* =$

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

°C	(Centipoises)	(Centistokes)	°F	(lb./ft-hr)	ft ² /hr
600	15.3* (Ref. 44)	7.77	1100	39.2*	0.3187
700	6.7*	3.45	1300	15.7*	0.1300
800	3.45	1.82	1500	7.6*	0.0641

Exponential Form (centipoises) $\mu = 0.00517e^{6976/T^{\circ}\text{K}}$

*Denotes experimental values. Other values given are calculated or estimated.

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
115	RbF BeF ₂	50 50	68.98 31.02	75.8	400°C (752°F)

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc) 2.85

LIQUID ($\rho = \text{gm/cc}$, $T = {}^\circ\text{C}$) $\rho = 2.75 - 0.00050T$

LIQUID ($\rho = \text{lbs}/\text{ft}^3$, $T = {}^\circ\text{F}$) $\rho = 172.2 - 0.0173T$

MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION ($1/{}^\circ\text{C} \times 10^4$) 2.08

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm) $H_T - H_0 {}^\circ\text{C}^*$ =

Heat Capacity (cal/gm ${}^\circ\text{C}$) $c_p^* =$

Heat Capacity at 300°C (572°F) $c_p = 0.22$

LIQUID

Enthalpy (cal/gm) $H_T - H_0 {}^\circ\text{C}^*$ =

Heat Capacity (cal/gm ${}^\circ\text{C}$) $c_p^* =$

Heat Capacity at 700°C (1292°F) $c_p = 0.31$

HEAT OF FUSION (cal/gm) $H_L - H_S^* =$

THERMAL CONDUCTIVITY

K (BTU/hr ft ${}^\circ\text{F}$)

VISCOSITY

${}^\circ\text{C}$	(Centipoises)	(Centistokes)	${}^\circ\text{F}$	(lb./ft-hr)	ft^2/hr
600	11.5* (Ref. 22)	4.69	1100	30.3*	0.1977
700	5.2*	2.17	1300	12.3	0.0821
800	2.75*	1.17	1500	6.1*	0.0417

Exponential Form (centipoises) $\mu = 0.00534e^{6701/T_{\text{OK}}}$

*Denotes experimental values. Other values given are calculated or estimated.

Mixture	Component	Mol %	Wt. %	Avg. M.W.	Liquidus Temp.
116	KF BeF ₂	79 21	82.30 17.70	55.8	730°C (1346°F)

DENSITY

SOLID AT ROOM TEMPERATURE (gm/cc)	2.38
LIQUID (ρ = gm/cc, T = °C)	$\rho = 2.32 - 0.00040T$
LIQUID (ρ = lbs/ft ³ , T = °F)	$\rho = 145.3 - 0.0139T$
MEAN VOLUMETRIC COEFFICIENT OF LIQUID EXPANSION (1/°C x 10 ⁴)	1.97

ENTHALPY, HEAT CAPACITY AND HEAT OF FUSION

SOLID

Enthalpy (cal/gm)	$H_T - H_0^{\circ}C^*$ =
Heat Capacity (cal/gm °C)	$c_p^* =$
Heat Capacity at 300°C (572°F)	$c_p = 0.27$

LIQUID

Enthalpy (cal/gm)	$H_T - H_0^{\circ}C^*$ =
Heat Capacity (cal/gm °C)	$c_p^* =$
Heat Capacity at 700°C (1292°F)	$c_p =$

<u>HEAT OF FUSION (cal/gm)</u>	$H_L - H_S^* =$
--------------------------------	-----------------

THERMAL CONDUCTIVITY

K (BTU/hr ft °F)

VISCOSITY

°C	(Centipoises)	(Centistokes)	°F	(lb./ft-hr)	ft ² /hr
800	2.2* (Ref.40)	1.10	1500	5.0*	0.0401

$$\text{Exponential Form (centipoises)} \quad \mu = 0.0770e^{3600/T^{\circ}\text{K}}$$

*Denotes experimental values. Other values given are calculated or estimated.

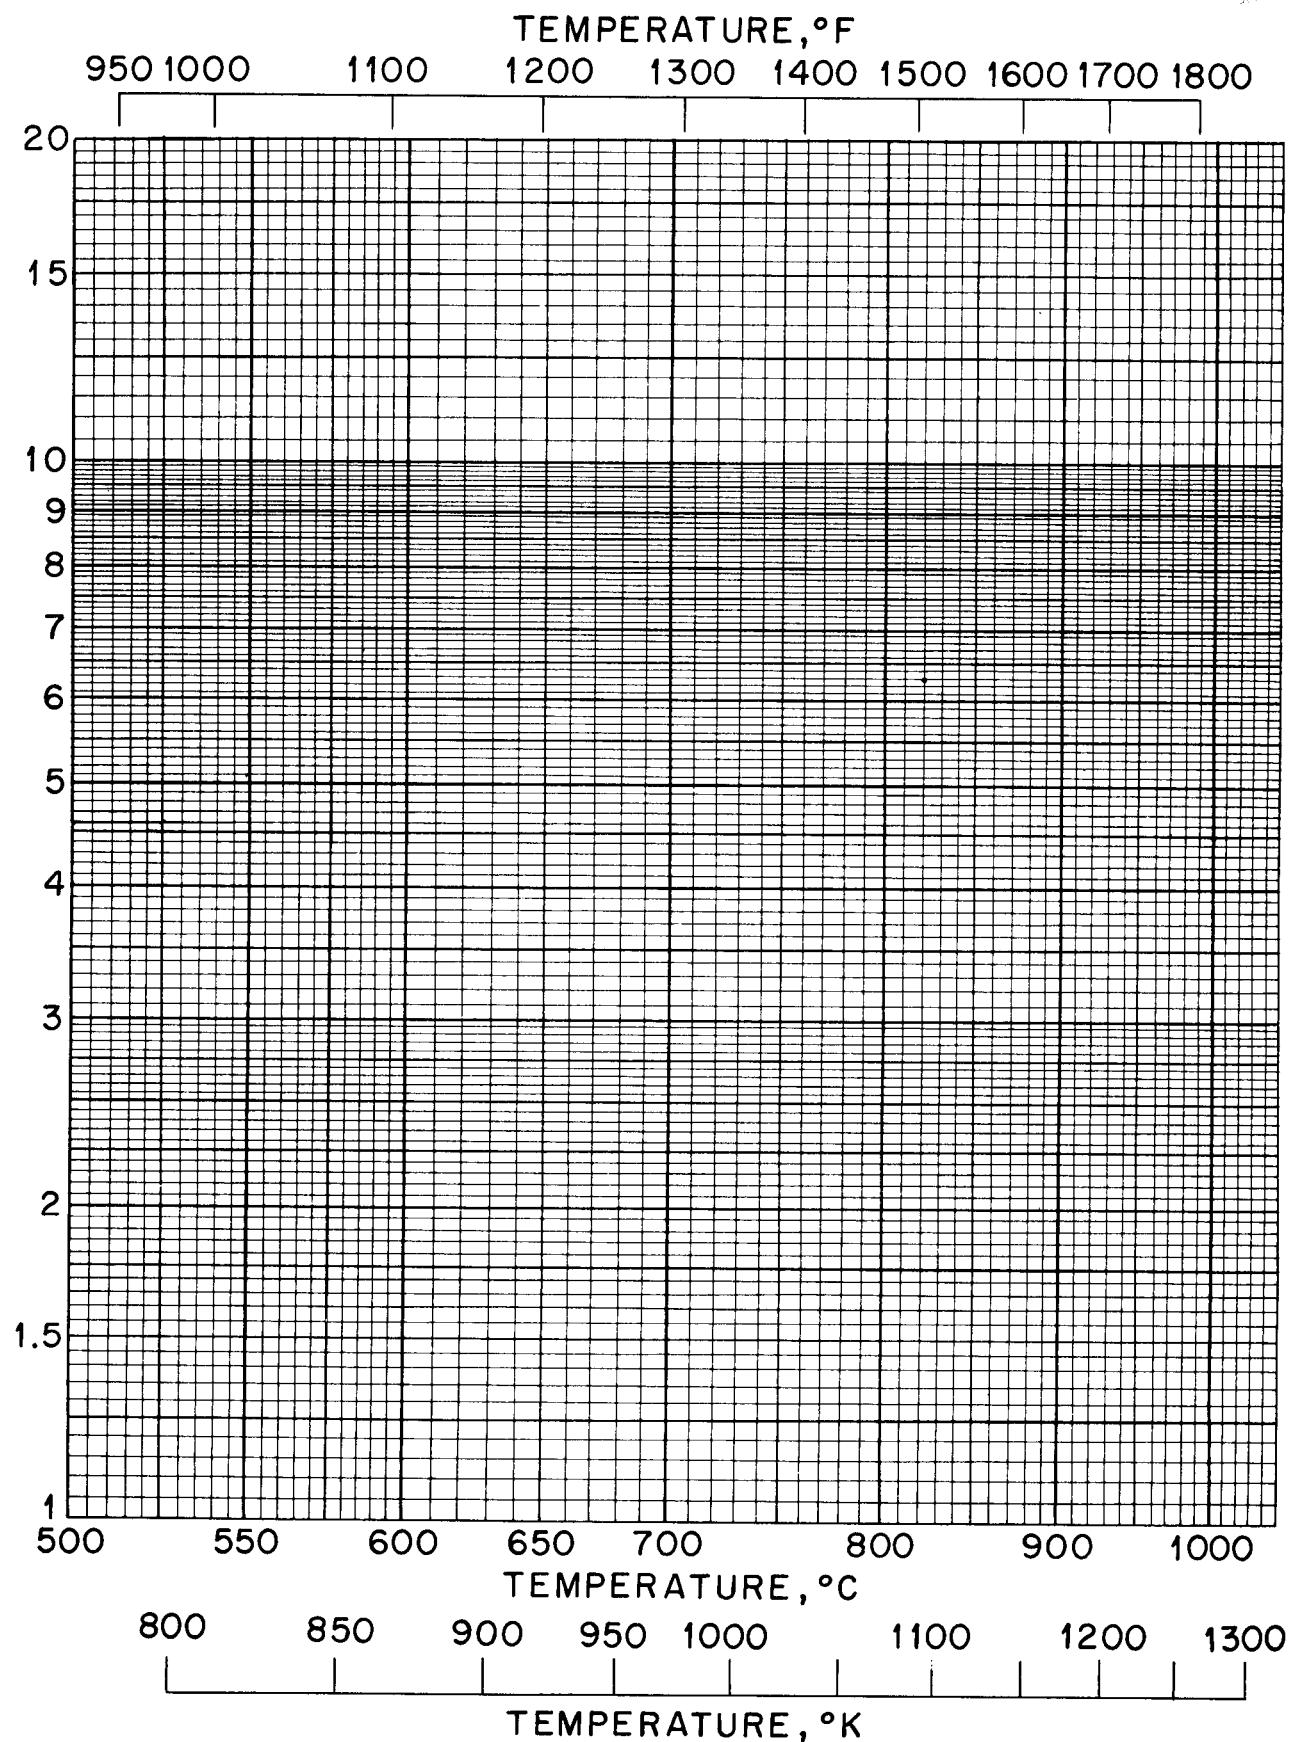


Figure I. Viscosity Worksheet

(This sheet of specially prepared graph paper has been included to facilitate interpolation and extrapolation of viscosity data).

CONCLUDING REMARKS

The summary of physical properties presented in this report has been compiled for the various technical groups within the ANP Project who need it. Properties have been measured or predicted for a large portion of the fluoride systems that have been of interest to the Project thus far. It is anticipated that more measurements will be made for new fluoride systems as they become attractive.

In the meantime, however, in most cases the thermal properties of such new fluoride systems can be estimated satisfactorily for preliminary design purposes with the aid of the correlation relations that have been developed. For example, molten densities have been related uniquely to room temperature densities or molecular weight which can be calculated (see topical report, ORNL 1702). The heat capacities were found to be inversely proportional to the average molecular weight and directly proportional to the average number of atoms in the mixture (see topical report, ORNL 1956).

Topical reports on the viscosity and thermal conductivity research on fluorides are being prepared. Viscosities have been found to vary with molecular weight and also with molar volume along the lines indicated by the Batchinski relation. The thermal conductivities have been found to vary inversely with average molecular weight. In addition, liquid thermal conductivities have been proportioned into atomic and ionic contributions each of which has been separately correlated.

REFERENCES

1. C. J. Barton, ORNL CF 55-9-78.
2. C. J. Barton, personal communication.
3. B. C. Blanke, MLM CF 55-11-14.
4. W. D. Powers, G. C. Blalock, ORNL 1956, January 11, 1956.
5. M. Tobias, S. I. Kaplan, S. J. Claiborne, ORNL CF 52-3-230.
6. S. I. Kaplan, ORNL CF 51-8-97.
7. M. Tobias, ORNL CF 51-7-169.
8. S. I. Cohen, T. N. Jones, ORNL CF 55-4-32.
9. National Research Council--Bulletin 118, "Data on Chemicals for Ceramic Use", 1949.
10. S. I. Cohen, T. N. Jones, ORNL CF 53-7-126.
11. L. Cooper, S. J. Claiborne, ORNL CF 52-8-163.
12. S. I. Cohen, T. N. Jones, ORNL CF 56-5-33.
13. N. D. Greene, ORNL CF 54-8-64.
14. S. J. Claiborne, ORNL CF 53-1-233.
15. J. Cisar, ORNL CF 51-11-78.
16. S. I. Cohen, T. N. Jones, ORNL 1702, July 19, 1954.
17. J. Cisar, ORNL CF 51-11-198.
18. J. Cisar, personal communication.
19. S. I. Cohen, T. N. Jones, ORNL CF 55-2-20.
20. S. I. Cohen, T. N. Jones, ORNL CF 56-4-148.
21. S. I. Cohen, T. N. Jones, ORNL CF 53-3-259.
22. S. I. Cohen, T. N. Jones, unpublished data.
23. R. F. Redmond, T. N. Jones, ORNL CF 52-11-105.
24. S. I. Cohen, T. N. Jones, ORNL CF 55-12-128.
25. S. I. Cohen, ANP Quarterly Progress Report for Period Ending December 10, 1955, ORNL 2012, page 180.
26. S. J. Claiborne, ORNL CF 52-11-72.
27. S. I. Cohen, T. N. Jones, ORNL CF 55-2-89.
28. S. I. Cohen, T. N. Jones, ORNL CF 55-3-137.
29. W. D. Powers, S. J. Claiborne, ORNL CF 54-10-139.
30. S. I. Cohen, T. N. Jones, ORNL CF 55-9-31.
31. S. I. Cohen, T. N. Jones, ORNL CF 55-3-61.
32. S. I. Cohen, T. N. Jones, ORNL CF 55-5-59.
33. W. D. Powers, G. C. Blalock, ORNL CF 56-5-68.
34. S. I. Cohen, T. N. Jones, ORNL CF 55-5-58.

35. B. C. Blanke, personal communication.
36. S. I. Cohen, T. N. Jones, ORNL CF 55-7-33.
37. W. D. Powers, G. C. Blalock, ORNL CF 55-11-68.
38. S. I. Cohen, T. N. Jones, ORNL CF 55-11-27.
39. S. I. Cohen, T. N. Jones, ORNL CF 55-8-21.
40. S. I. Cohen, T. N. Jones, ORNL CF 55-11-28.
41. S. I. Cohen, T. N. Jones, ORNL CF 55-12-127.
42. W. D. Powers, G. C. Blalock, ORNL CF 56-5-67.
43. W. D. Powers, S. J. Claiborne, ORNL CF 54-7-145.
44. S. I. Cohen, T. N. Jones, ORNL CF 55-8-22.
45. W. D. Powers, S. J. Claiborne, R. M. Burnett, unpublished data.
46. K. K. Kelley, Contributions to the Data on Theoretical Metallurgy, Bureau of Mines Bulletin 476, 1949.
47. T. B. Douglas, J. L. Dever, Thermal Conductivity and Heat Capacity of Molten Materials, Part 1, The Heat Capacity of Lithium Fluoride From 0°C to 900°C, WADC 53-201, Part 1, October 1953.
48. H. F. Poppendiek, ANP Quarterly Progress Report for Period Ending March 10, 1956, ORNL 2061, page 179.
49. M. W. Rosenthal, H. F. Poppendiek, R. M. Burnett, ORNL CF 54-11-63.