

**A NEW METHOD FOR MANUFACTURING
DEPLETED URANIUM DIOXIDE-STEEL CERMET CASKS
FOR SPENT NUCLEAR FUEL AND RADIOACTIVE WASTES**

Charles W. Forsberg
Oak Ridge National Laboratory*
P.O. Box 2008
Oak Ridge, Tennessee 37831-6165
Tel: (865) 574-6783; E-mail: forsbergcw@ornl.gov

Vinod Sikka
Oak Ridge National Laboratory
P.O. Box 2008
Oak Ridge, Tennessee 37831-6083
Tel: (865) 574-5112; E-mail: sikkavk@ornl.gov

Manuscript Date: March 12, 2004
File Name: Manufacture.DUuser.Conf2004.Paper

Paper Prepared for
Depleted Uranium Users Conference
American Society of Manufacturing
Oak Ridge, Tennessee
April 20-22, 2004

The submitted manuscript has been authored by a contractor of the U.S. Government under contract DE-AC05-00OR22725. Accordingly, the U.S. Government retains a nonexclusive, royalty-free license to publish or reproduce the published form of this contribution, or allow others to do so, for U.S. Government purposes.

*Oak Ridge National Laboratory, managed by UT-Battelle, LLC, for the U.S. Department of Energy under contract DE-AC05-00OR22725.

A NEW METHOD FOR MANUFACTURING DEPLETED URANIUM DIOXIDE-STEEL CERMET CASKS FOR SPENT NUCLEAR FUEL AND RADIOACTIVE WASTES

Charles W. Forsberg and Vinod Sikka
Oak Ridge National Laboratory
Oak Ridge, Tennessee 37831-6165
Tel: (865) 574-6783; E-mail: forsbergcw@ornl.gov

ABSTRACT

Cermets using depleted uranium dioxide (DUO₂) and other ceramics embedded in a steel matrix are being investigated as materials of construction for (1) spent nuclear fuel (SNF) storage, transport, disposal, and multifunction casks and (2) casks for gamma-emitting radioactive wastes. Cermet cask performance (capacity for a given weight limit, capacity for a given size limit, resistance to assault, etc.) may significantly exceed the performance of casks constructed of more traditional materials such as steel. The principal viability issue is manufacturing costs. A new powder metallurgy method for fabricating large casks has been invented (patents applied for) that may result in low fabrication costs. Its potentially favorable economics are a result of (1) a process that produces a near-final-form cask with a minimum number of processing steps and (2) the low cost of the starting materials.

1. INTRODUCTION

Cask performance ultimately depends upon the available materials of construction. Investigations of the characteristics of casks made of cermets (ceramics embedded in a metal matrix) show the potential for superior performance compared with casks constructed of other materials. The potential advantages of cermet casks include capacity for greater quantities of SNF per cask, given a defined cask weight or size limit, and resistance to assault. Historically, cermets are used in very severe operating environments: (1) tank and vault armor, (2) brake shoes, (3) tool bits, and (4) nuclear fuel in some test reactors. As a consequence, the properties of cermets are known and thus the characteristics of cermet casks can be evaluated.

While the potential performance of cermets is outstanding, the viability of using such a high-performance material depends upon the development of low-cost reliable cask fabrication technologies. A new powder metallurgy method invented for cask fabrication (Forsberg and Sikka, January 2003) is now being investigated. This paper discusses the cask market; the cermet requirements, which in turn, determine the requirements on the fabrication process; and the new fabrication process.

2. MARKETS

The potential market for a product must be significant to justify development of new technologies. The market for casks is expected to grow rapidly.

2.1 Spent Nuclear Fuel

The waste from generation of electricity using nuclear energy is SNF. A large reactor generates about 30 tons per year of this highly radioactive waste that must be stored, shipped, and ultimately disposed of in a geological repository. Traditionally, the SNF has been stored in pools at the reactor and shipped using steel casks with wall thicknesses of 10s of centimeters and gross weights of - 100 metric tons. Strong incentives exist today to develop improved SNF storage and transport casks.

- *Increased demand.* Because of the potential for a large increase in the demand for SNF casks, there are strong incentives to improve cask economics and consider serial manufacture (vs piecework) of casks. Four interconnected markets exist. First, at-reactor SNF storage pools are reaching their capacity and SNF is increasingly being placed in dry storage casks at the reactor. Second, the planned Yucca Mountain repository is expected to become operational within the next decade creating a growing demand for transport casks. Third, much of the SNF must be aged (stored) at the repository before disposal. The capacity of the repository is limited by the SNF decay heat which decreases with time. Aging the SNF before disposal reduces decay heat, simplifies operations, and increases repository capacity. Last, advanced SNF management systems have been proposed (Forsberg and Dole, October 2003) that use multipurpose casks for storage, transport, and disposal. Adoption of such a system would require casks for all SNF.
- *Replacement of existing SNF storage facilities.* As a consequence of the events of September 11, 2001, the requirements for and cost of SNF security are increasing. Casks offer potentially superior resistance to assault and have lower operational security costs than pool storage of SNF. Changing requirements are changing the economics and thus may create a storage cask market to replace other existing SNF storage facilities.
- *New markets.* SNF decay heat decreases with time. Short-cooled SNF has historically been stored in pools to assist in heat removal. Although casks have traditionally had limited capability to remove decay heat, improved cask cooling (Forsberg, June 2004) is an enabling technology to allow the storage of hotter SNF in casks and thus potentially expand the SNF cask market into storage of shorter-cooled SNF.

2.2 Gamma-Emitting Radioactive Wastes

The United States has significant inventories of remote-handled transuranic wastes. The Waste Isolation Pilot Plant currently disposes of contact-handled transuranic waste. Packaging of the remote-handled transuranic wastes in disposable cermet waste packages (WPs) would allow these wastes to be treated as contact-handled wastes. This would allow the existing facilities and operations to dispose of these wastes. For this particular application, the use of depleted uranium (DU) in the WP also reduces long-term concerns associated with nuclear criticality (Forsberg and Dole, October 2003).

3. CERMET CASKS

The functional requirements for an SNF cask include a handling package for the SNF, radiation shielding, cooling the SNF to limit its peak temperatures, and physical protection. Handling facilities at the reactor restrict the weight of the cask to - 100 tons. The physical size is limited by facility constraints at the reactor and by rail shipping requirements.

Cermet SNF casks have the potential for very high performance compared with casks constructed of traditional materials. The cermet (Fig. 1) consists of DUO_2 ceramic particulates and other particulates (graphite, silicon carbide, etc.), if needed, embedded in a steel matrix between two clean layers of steel. The outstanding performance of cermets follows from their intrinsic characteristic: the ability to encapsulate variable quantities of different ceramic particulates (including brittle ceramics) into a strong high-integrity ductile metal matrix. Each component is optimized to meet specific cask requirements. The various incentives for cermet casks and the corresponding technical requirements imposed on the cermet and the manufacturing method are discussed herein.

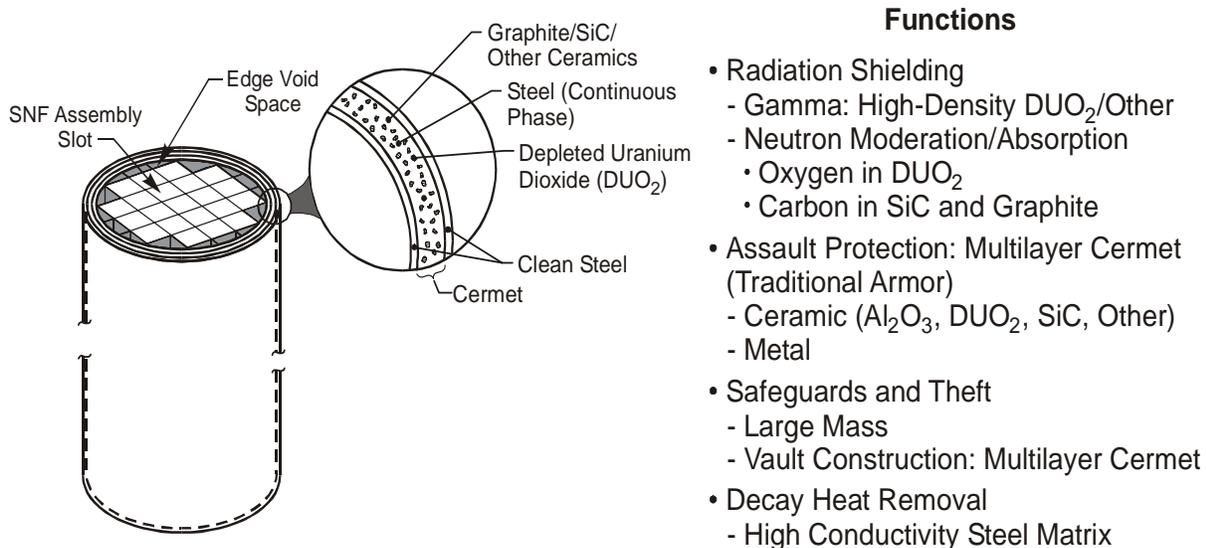


Fig. 1. Depleted uranium dioxide–steel spent nuclear fuel cask.

3.1 Minimize Cask Weigh

SNF cask capacity is usually limited by weight. Facility limitations, such as cranes, determine the maximum gross cask weight. If the cask weight can be reduced, the number of SNF assemblies per cask can be increased with the same gross (loaded) cask weight. Cask weight is primarily determined by gamma shielding requirements where, to a first approximation, the required shielding can be defined in terms of required mass per unit area (g/cm^2) to stop the gamma radiation. If this were the only consideration, cask weight would be independent of the density of the shielding material. However, two geometric effects are also present.

- *Cask diameter.* The “area” requiring shielding is a variable. Excluding end effects, if the shielding material had no thickness, the area would be defined as follows: πH inner diameter of the cask H cask height. However, shielding materials have various thicknesses. At a distance of 1 cm into the shielding the area is πH (inner diameter of the cask + 2 cm) H height. The further from the inner cask surface, the more shielding material is required per centimeter of cask thickness because the cask circumference increases as one moves out from the inner cask diameter. There are also geometric cask end effects. As a consequence, cask weight can be minimized by using high-density shielding materials with minimum cask shield thicknesses. As a high-density ceramic, DUO₂ has major advantages: a density significantly greater than that of steel, the matrix material; compatibility with the cermet manufacturing process; chemical stability; available in large quantities (500,000 tons excess DU in storage); and a relatively low cost.
- *SNF characteristics.* The gamma radiation from an SNF assembly is highest at the center and lowest at the ends. To minimize cask weight, shielding density should vary with cask elevation, with the greatest density of shielding present near the midline. The cermet allows variable density with cask height by the choice of ceramics and the volume fraction of the cask that is a ceramic. High-density ceramics (such as DUO₂) are required near the cask centerline. To minimize weight, no ceramics (only steel) or low-density ceramics (such as Al₂O₃) can be used near the ends of the cask, particularly the outer edges far from the SNF. This requires that the fabrication process be able to produce variable-composition cermets.

3.2 Minimize Cask Size

Cask size should be minimized to avoid handling and transport constraints, primarily rail constraints. The cask wall thickness is controlled by the amount of gamma and neutron shielding required. High-density materials minimize the cask wall thickness for gamma shielding while different types of materials are required for neutron shielding. By slowing and then capturing neutrons, oxygen, carbon, silicon, and other additives in cermets provide enhanced neutron shielding compared with steel. In ceramics such as DUO₂, oxygen (normally not considered a neutron moderator) has a high density and thus can assist neutron moderation. Neutron absorbers, such as rare earth oxides, can also be added to the cermet for neutron absorption. Depending upon the SNF burnup, the ceramics in the cermet can provide significant neutron shielding.

3.3 Maximize Resistance to Assault

Many types of armor, such as that used in Russian main battle tanks, are made of cermets in which the ceramic and metal components are selected to address different kinds of threats (Forsberg and Landingham, November 2002). Armor made of a single material can be more easily defeated because it is possible to target the weaknesses of the specific material. In traditional cermet armors, the ceramic is a hard material that breaks up the incoming projectile or explosive charge and spreads the forces over a wider area. However, hard materials are generally brittle and do not absorb much energy. The ductile metal then absorbs the energy while the inhomogeneous characteristic of the cermet breaks up shock waves. The optimum armor has variable ceramic particle sizes, compositions, and volume fractions with depth; thus, the ideal cermet fabrication process should allow production of a variable-composition cermet.

3.4 Waste Management

If a cermet cask is used as an SNF WP, the DUO₂ and iron in a cermet disposal cask can slow the degradation of SNF over time under repository conditions and reduce long-term migration of radioactive nuclides (Forsberg and Dole, October 2003). For both SNF and transuranic wastes, the DUO₂ reduces the potential for long-term repository criticality. Use of DUO₂ in a WP has the additional benefit of allowing for disposal of excess DU (with the potential for economic credit for avoided disposal costs) while providing other benefits to the repository.

4. NEW MANUFACTURING METHOD

The economic viability of cermet casks depends upon manufacturing costs. If the manufacturing costs are sufficiently low, cermet casks become a preferred cask technology. Cermet properties and characteristics are well known. Uranium dioxide cermet nuclear fuels have been successfully manufactured for many test reactors (Forsberg et al., September 2001) using traditional powder metallurgical techniques. However, the traditional cermet fabrication methods are expensive for construction of large casks because cermet plates are must first be produced and then fabricated into casks. The traditional powder metallurgical technique involves (1) mixing the metal powders and ceramic particulates, (2) enclosing the mixture in some type of close-fitting metal box, (3) heating the mixture while removing the gases between the particulates by vacuum, and (4) compressing the box and mixture at high temperatures to create a monolithic matrix of metal plate that encapsulates ceramic particulates. The plates must then be fabricated into casks; however, cermets are very difficult to form and weld. The multistep process thus results in increased costs.

Two new methods (Forsberg, C. W. and V. K. Sikka, April 2003) for cermet cask fabrication are being investigated: a method involving casting a cermet and a new (patent pending) powder metallurgy method (Forsberg and Sikka, January 2003). The new powder metallurgy method (Fig. 2) is described herein. The potential favorable economics are a result of (1) a process that produces a near-final-form cask, which minimizes the number of processing steps, and (2) the low cost of the starting materials. While the fabrication technique is new, the cermet forming processes on a microscopic scale (temperatures, pressures, material compositions) are the same as those associated with the traditional processes. The new process consists of the following steps.

- *Preform fabrication.* A preform slightly larger than the final annular cask body is constructed of steel and serves as the inner and outer layer of clean steel in the final cask. The preform consists of the inside, outside, and top surfaces of the cask body but excludes the cask bottom.
- *Preform filling.* The preform is filled with a particulate mixture of DUO₂, other ceramics, and steel powder. A schematic of the filling process is shown in Fig. 3. The upside-down cask preform is placed on a table that can be rotated. The particulate distribution heads of the fill machine are lowered to the bottom of the preform. As the table rotates, the fill machine (1) feeds particulate mixes (steel and ceramic particulates) to the preform in a continuous layer that is several centimeters deep, (2) compacts each layer as it placed in the preform, and (3) is withdrawn as the preform is filled with a continuous spiral particulate layer from the bottom of the preform to the top. Many rotations are required to fill the preform. The use of multiple particulate feed nozzles makes it possible to vary the composition of individual layers from the inside of the cask preform to the outside. The composition of the particulate mix can also be varied in the vertical direction. In fact, this design allows the fill machine to vary particulate composition throughout the entire preform. The compaction is to ensure no movement of the particulate fill occurs during subsequent handling operations. The gas composition within the preform is maintained under chemically reducing conditions to avoid oxidation of the steel powder.

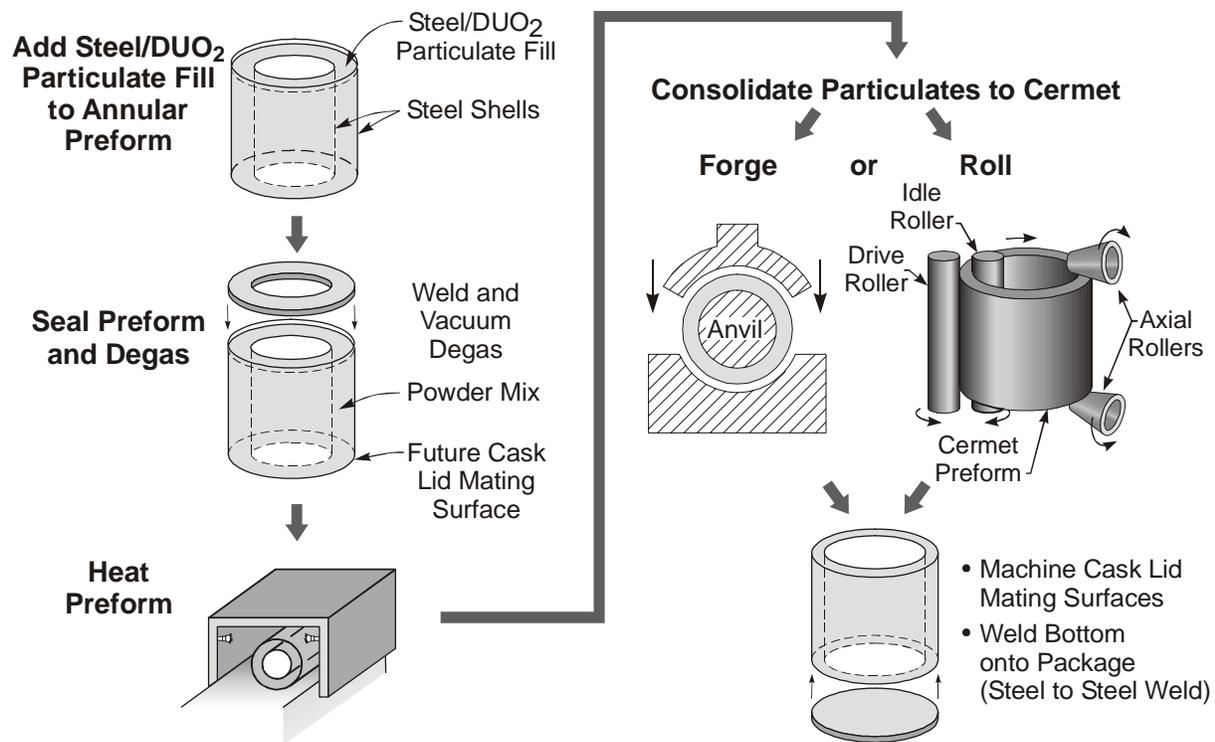


Fig. 2. New method for the manufacture of DU dioxide-steel SNF cask.

- *Welding, heating, and gas evacuation.* After the preform is filled, an annular ring is welded to the preform to create a loaded, sealed annular preform. The preform is then evacuated while being heated, which removes gases in the void spaces in the particulate mixture and those gases sorbed on the particulates.
- *Forging.* The preform is heated and compressed to (1) eliminate all void spaces and (2) weld the metal particles together to form a continuous, strong steel matrix containing various ceramic particulates. The compression is performed at high temperatures to (1) minimize the forces necessary to eliminate all voids in the particulate mixture and (2) rapidly weld the steel particulates into a solid matrix by solid-state diffusion. Figure 4 shows the yield strength of mild steel vs temperature. As can be seen, heating the preform dramatically reduces the forces required to consolidate the particulate mixture into a cermet. The forging temperature is significantly below the melting point of the metal. If this were a molten system, the high-density ceramics would sink to the bottom and the low-density ceramics would float on the surface of the molten metal. It is the powder metallurgy technique that allows the variable composition cermet to be fabricated. Two standard industrial processes to consolidate the preform and particulate mixture currently exist.

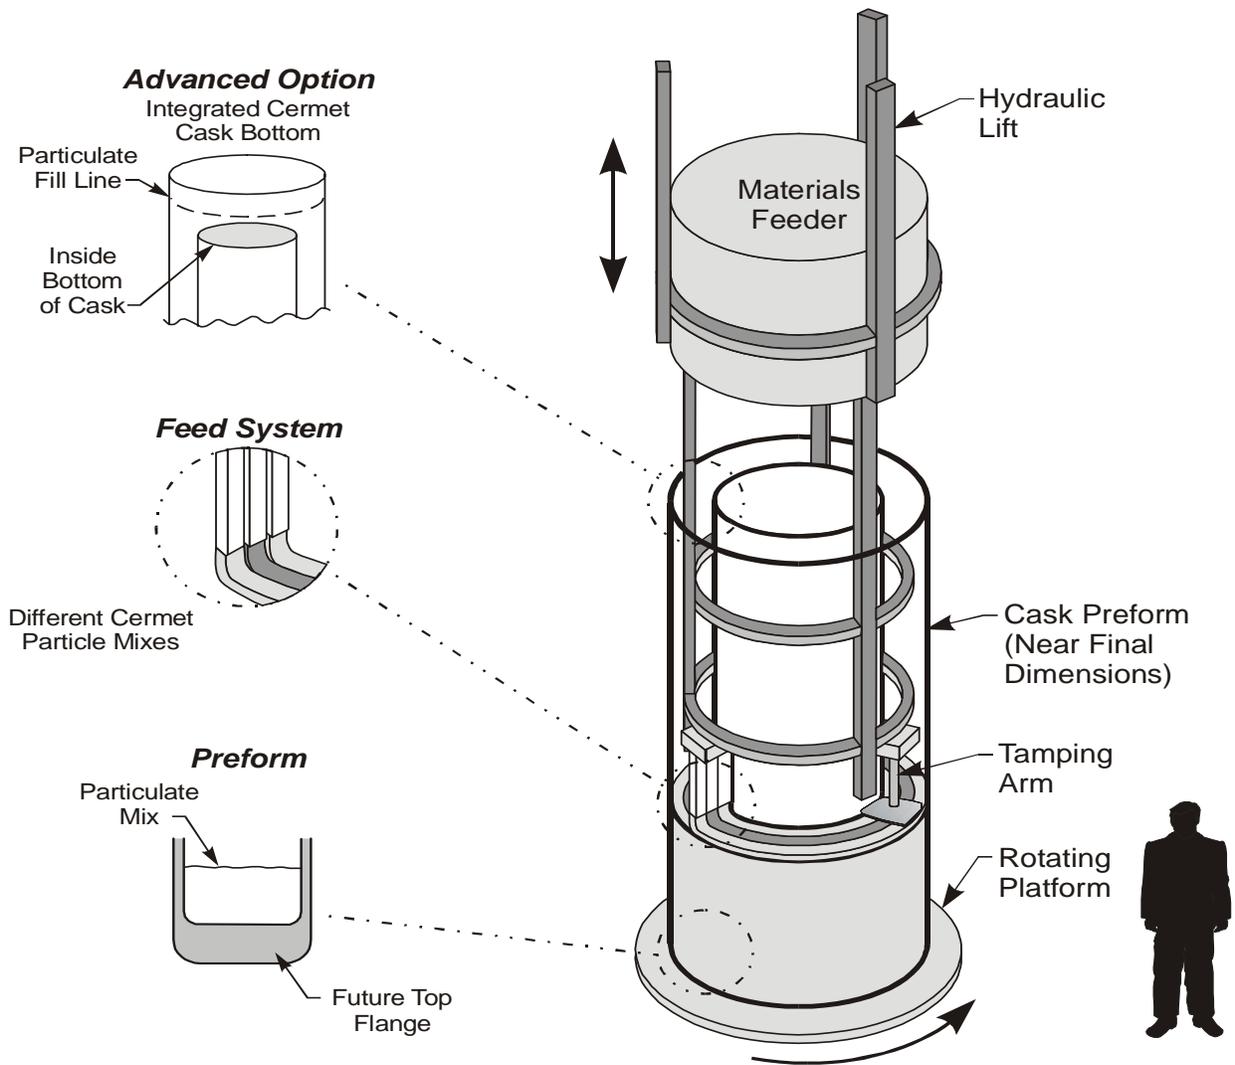


Fig. 3. Loading of the cermet preform with variable particulate compositions of DUO_2 , other ceramics, and steel powder.

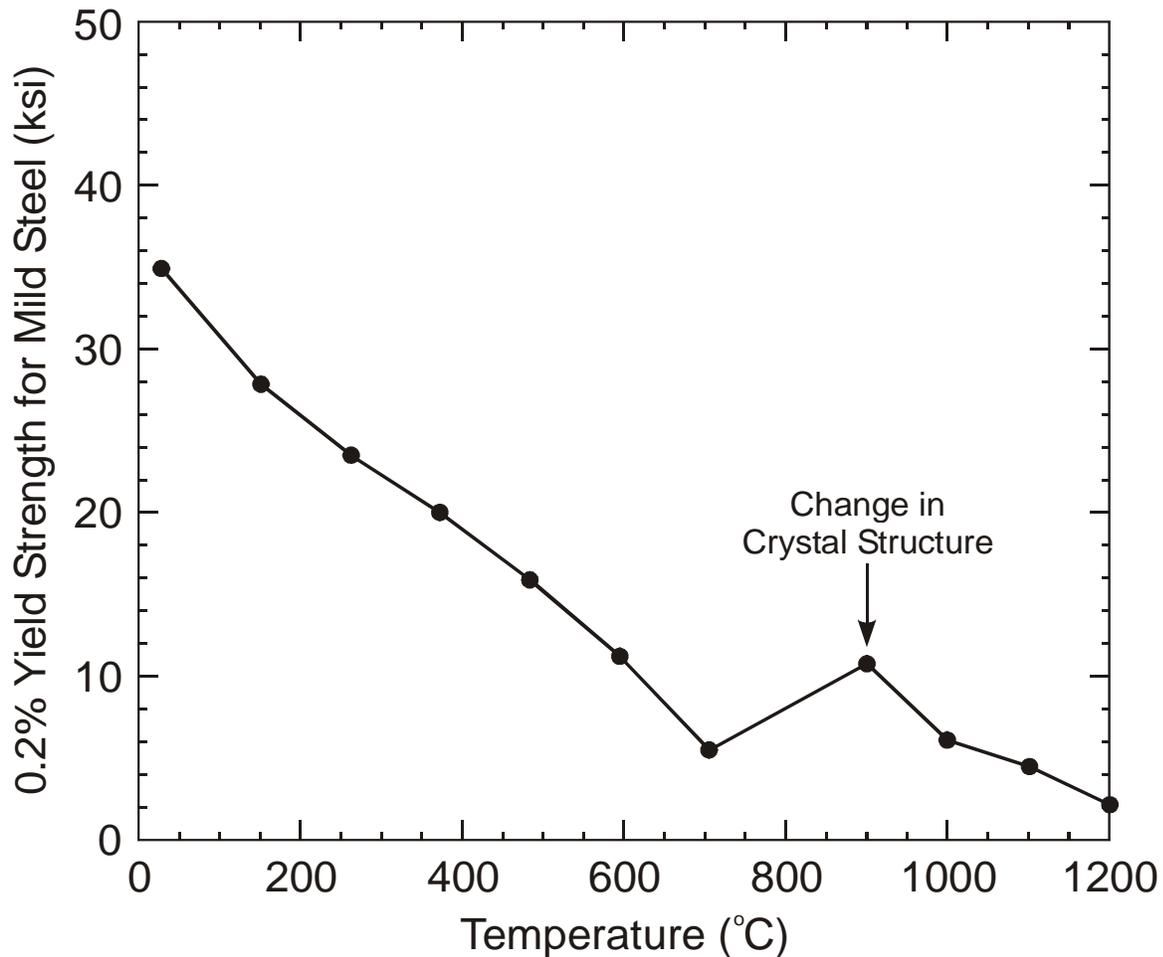


Fig. 4. Yield strength of mild steel vs temperature.

- Traditional forging. The hot heated perform can be hammered to consolidate the particulate mixture into a cermet and produce the final cask form. In one method (shown in Fig. 2), a cylindrical anvil the size of the interior of the final cask is placed inside the preform. The forge then strikes the exterior to consolidate the particulate mixture. While the cask may weigh 100 tons, forges in the United States can form parts up to 500 tons in weight.
- Ring-rolling forging. The hot loaded preform can be placed in a ring-rolling machine and rolled to its final form (Fig. 2).

- *Finishing.* The cask bottom is welded onto the cylindrical cask body. After completion of this step, a vertical boring mill is used to obtain the final dimensions and to drill holes in the top of the cask for the lid bolts. While the steel preform thickness in the center of the cask may be 1 to 2 cm, the preform thickness near the lid may be 10 to 20 cm to allow for bolt holes and attachment of other hardware. All welding and machining operations are performed on the preform, not on the internal cermet. This avoids the very difficult operations of welding or machining cermets.

Many fabrication variants exist. The preform can include the bottom of the cask (Fig. 3). Note that the cask body is positioned upside down during the fill operation. Although this technique allows the fabrication of a preform that incorporates the cask bottom, more-sophisticated forging operations are required to produce an integral bottom and side cermet cask.

This cask fabrication process has several defining characteristics. The fabrication technique allows the use of variable cermet compositions within the cask body to optimize properties. No cermet welding is required, and because the cask body produced via the forging process is very close to the final dimensions, machining and waste generation is minimized.

In terms of manufacturing, this powder metallurgical method limits the handling of radioactive DUO_2 to the process of filling the preform, a room-temperature operation that requires limited space and limited capital investment and generates little radioactive waste. All of the remaining operations involve handling and processing of a sealed container with DUO_2 . Such a process restricts the health physics operations required for handling the DUO_2 to a very small area and may allow the use of commercial shops for the forging and machining steps. This, in turn, limits the front-end investment—a major concern with a new enterprise.

Powder metallurgy production techniques have the potential for low costs. Millions of tons of iron and steel powders are produced for the fabrication of many products; thus, the costs of raw materials are low. The current cost for steel powder purchased in large quantities is about \$600/ton.

5. CONCLUSIONS

Cermet casks for SNF and gamma-emitting wastes have major performance advantages compared with casks constructed of more conventional materials. This includes (1) greater capacity for casks of a fixed weight and size and (2) improved resistance to assault or accidents. The primary challenge is to develop a low-cost cermet cask fabrication method. A new cask fabrication method has been invented that produces a near-final-form cask and avoids the need to work or weld cermets. Development efforts have begun, but significant work remains.

ACKNOWLEDGMENTS

This work was done under the auspices of the U.S. Department of Energy Depleted Uranium Uses Research and Development Program. Additional information (including technical reports) is available at <http://web.ead.anl.gov/uranium>.

REFERENCES

Forsberg, C. W., June 2004, "A Multifunction Cask for At-Reactoer Storage of Short-Cooled Spent Fuel, Transport, and Disposal," 2004 International Congress on Advances in Nuclear Power Plants (ICAPP '04), Embedded International Topical Meeting, 2004 American Nuclear Society Annual Meeting, Pittsburgh, Pennsylvania, June 13-17, 2004.

Forsberg, C. W. and L. R. Dole, October 2003, "An Integrated Once-Through Fuel-Cycle with Depleted Uranium Dioxide SNF Multifunction Casks," *Proc. Advances in Nuclear Fuel Cycle Management III, Hilton Head Island, South Carolina, October 5-8, 2003*, American Nuclear Society, La Grange Park, Illinois.

Forsberg, C. W. and R. L. Landingham, November 2002, "Depleted Uranium Dioxide-Steel Cermet Multipurpose Casks for Enhanced SNF Protection," p. 313 in *Trans. American Nuclear Society 2002 Winter Meeting, Washington, D.C., November 17-21, 2002*.

Forsberg, C. W. and V. K. Sikka, January 2003, *Manufacture of Annular Cermet Objects, Patent Application to the U.S. Patent Office*, January 16, 2003.

Forsberg, C. W. and V. K. Sikka, April 2003, "Alternative Manufacturing Methods for Depleted Uranium Dioxide-Steel Cermet SNF Casks," *Proc. 10th International High-Level Radioactive Waste Conference, Las Vegas, Nevada, March 30-April 2, 2003*, American Nuclear Society, La Grange Park, Illinois.

Forsberg, C. W., L. B. Shappert, P. Byrne, and B. Broadhead, September 2001, "Cermet Transport, Storage, and Disposal Packages Using Depleted Uranium Dioxide and Steel," *Proc. of the 13th International Symposium on the Packaging and Transport of Radioactive Materials, Chicago, Illinois*, Institute of Nuclear Materials Management, Northbrook, Illinois, September 2001.